

3-20-2016

Advanced Bridge Safety Initiative: Phase 2 Task 1 Rivet Testing of Rivets Taken from Maine Truss Bridge, 2016

Maine Transportation Research Division

Maine Department of Transportation

Scott Tomlinson

Follow this and additional works at: https://digitalmaine.com/mdot_docs

Recommended Citation

Maine Transportation Research Division; Maine Department of Transportation; and Tomlinson, Scott, "Advanced Bridge Safety Initiative: Phase 2 Task 1 Rivet Testing of Rivets Taken from Maine Truss Bridge, 2016" (2016). *Transportation Documents*. 111. https://digitalmaine.com/mdot_docs/111

This Text is brought to you for free and open access by the Transportation at Digital Maine. It has been accepted for inclusion in Transportation Documents by an authorized administrator of Digital Maine. For more information, please contact statedocs@maine.gov.



Transportation Research Division



Technical Report 16-14

Advanced Bridge Safety Initiative: Phase 2

Task 1

Rivet Testing of Rivets Taken from Maine Truss Bridge

March 2016

1. Report No. ME 16-14	2.	3. Recipient's Accession No.	
4. Title and Subtitle Advanced Bridge Safety Initiative: Phase 2, Task 1 - Rivet Testing of Rivets Taken from Maine Truss Bridge		5. Report Date March 2016	
		6.	
7. Author(s) Scott Tomlinson P.E., William Davids Ph.D, P.E.		8. Performing Organization Report No. 16-21-1332	
9. Performing Organization Name and Address Advanced Structures and Composites Center University Of Maine 35 Flagstaff Rd. Orono, ME 04469		10. Project/Task/Work Unit No. Project 017666.00	
		11. Contract © or Grant (G) No. Contract # 20160617*4564	
12. Sponsoring Organization Name and Address Maine Department of Transportation		13. Type of Report and Period Covered	
		14. Sponsoring Agency Code	
15. Supplementary Notes			
16. Abstract (Limit 200 words) <p>The Maine Department of Transportation (MaineDOT) has removed 25 rivets from an existing, older truss bridge. Many such truss bridges have low rating factors as determined using Federal Highway Administration (FHWA) and the American Association of State Highway and Transportation Officials (AASHTO) guidelines due to the assumption of conservatively low rivet strength properties in the absence of known properties. To provide the MaineDOT with better information regarding rivet properties, The University of Maine (UMaine) has tested the rivets in tension to determine their strength properties. Work conducted under this task included assessing the best test method based on existing literature, fabricating test fixtures, machining test specimens from each rivet, conducting the strength tests, determining rivet strength properties from the test data, and reporting the test results to the MaineDOT in this report.</p> <p>Rivet testing was conducted according to ASTM F606 Standard Test Methods for Determining the Mechanical Properties of Externally and Internally Threaded Fasteners, Washers, Direct Tension Indicators, and Rivets [and ASTM E8 Standard Test Methods for Tension Testing of Metallic Materials with variations as noted in this report. Rivets were machined to produce tension specimen with threaded grips at each end and a turned-down shank with dimensions adjusted from the standards to match provided rivet specimen. Rivets were tested in tension and mean yield strength (0.2% offset) was found to be 43.7 ksi and mean ultimate strength was found to be 69.6 ksi.</p>			
17. Document Analysis/Descriptors Bridge load rating, truss bridge rivets, rivet testing		18. Availability Statement	
19. Security Class (this report)	20. Security Class (this page)	21. No. of Pages 35	22. Price

Rivet Testing of Rivets Taken from Maine Truss Bridge

Prepared for:
Mr. Dale Peabody P.E.
Director Transportation Research
Maine Department of Transportation
16 State House Station
August, ME 04333-0016

University of Maine's Advanced Structures and Composites Center
Report Number: 16-21-1332

2016-03-20-Rev00

Prepared by:

Scott Tomlinson PE SCWI
Research Engineer

Reviewed by:

Dr. William Davids PE
John C. Bridge Professor and Department Chair

This report shall not be reproduced, except in full, without the written approval of
University of Maine's Advanced Structures and Composites Center.

CONFIDENTIAL

*The University of Maine Advanced Structures and Composites Center is an ISO 17025 accredited testing laboratory,
accredited by the International Accreditation Service.*



Document Log

Name/ Organization	Date	Version	Action
Scott Tomlinson, Author William Davids, Reviewer	2016-03-20	Rev00	Initial release to Maine Department of Transportation.

Table of Contents

Executive Summary	4
1 Specimen Fabrication	5
2 Testing.....	6
3 Data Analysis.....	8
4 Detailed Test Results.....	12
Appendices.....	13
A.1 Specimen Dimensions	14
A.2 Load vs. Position Plots.....	16
A.3 Engineering Stress vs. Approximate Engineering Strain.....	21
A.4 Load vs. Position Yield Strength Calculation Plots	26
A.5 Engineering Stress vs. Approximate Engineering Strain Rate.....	31

Index of Figures

Figure 1: Machined rivet dimensional drawing.....	5
Figure 2: Typical machined rivet.....	6
Figure 3: Typical rivet testing setup	7
Figure 4: Typical rivet specimen after failure.....	7
Figure 5: Typical load vs. position plot	8
Figure 6: Typical engineering stress vs. approximate engineering strain.....	9

Figure 7: Typical yield curve	10
Figure 8: Typical strain rate plot.....	11

Index of Tables

Table 1: Rivet strengths	4
Table 2: Specimen test results.....	12
Table 3: Specimen measurement information	14
Table 4: Specimen measurements.....	15
Table 5: Calculated specimen dimensions.....	15

Acronyms

AASHTO: American Association of State Highway and Transportation Officials
FHWA: Federal Highway Administration
MaineDOT: Maine Department of Transportation
UMaine: The University of Maine

Executive Summary

The Maine Department of Transportation (MaineDOT) has removed 25 rivets from an existing, older truss bridge. Many such truss bridges have low rating factors as determined using Federal Highway Administration (FHWA) and the American Association of State Highway and Transportation Officials (AASHTO) guidelines due to the assumption of conservatively low rivet strength properties in the absence of known properties. To provide the MaineDOT with better information regarding rivet properties, The University of Maine (UMaine) has tested the rivets in tension to determine their strength properties. Work conducted under this task included assessing the best test method based on existing literature, fabricating test fixtures, machining test specimens from each rivet, conducting the strength tests, determining rivet strength properties from the test data, and reporting the test results to the MaineDOT in this report.

Rivet testing was conducted according to ASTM F606 Standard Test Methods for Determining the Mechanical Properties of Externally and Internally Threaded Fasteners, Washers, Direct Tension Indicators, and Rivets [1] and ASTM E8 Standard Test Methods for Tension Testing of Metallic Materials [2] with variations as noted in this report. Rivets were machined to produce tension specimen with threaded grips at each end and a turned-down shank with dimensions adjusted from the standards to match provided rivet specimen. Rivets were tested in tension and mean yield strength (0.2% offset) was found to be 43.7 ksi and mean ultimate strength was found to be 69.6 ksi. A summary of results is presented in Table 1. Note that these values are for as-procured and tested specimen, and there may be unknown effects due to the flame cutting and extraction that could cause variations compared to in-situ rivets.

Table 1: Rivet strengths

Strength (23 Samples)	Mean (ksi)	Std. Dev. (ksi)	COV %
F_y Yield (0.2% Offset)	43.7	9.91	22.7
F_u Ultimate	69.6	4.60	6.60

For comparison, the Manual for Bridge Evaluation 2011 Second Edition AASHTO [3] gives F_u for: “Unknown rivet type and origin” as 50 ksi, Carbon Steel ASTM A141 or ASTM A502 Grade I as 60 ksi, and ASTM A502 Grade II as 80 ksi.

1 Specimen Fabrication

Due to the size of the rivets extracted, the specimens were prepared according to Figure 1 in January 2016 by the Advanced Manufacturing Center at UMaine. A typical machined rivet is shown in Figure 2.

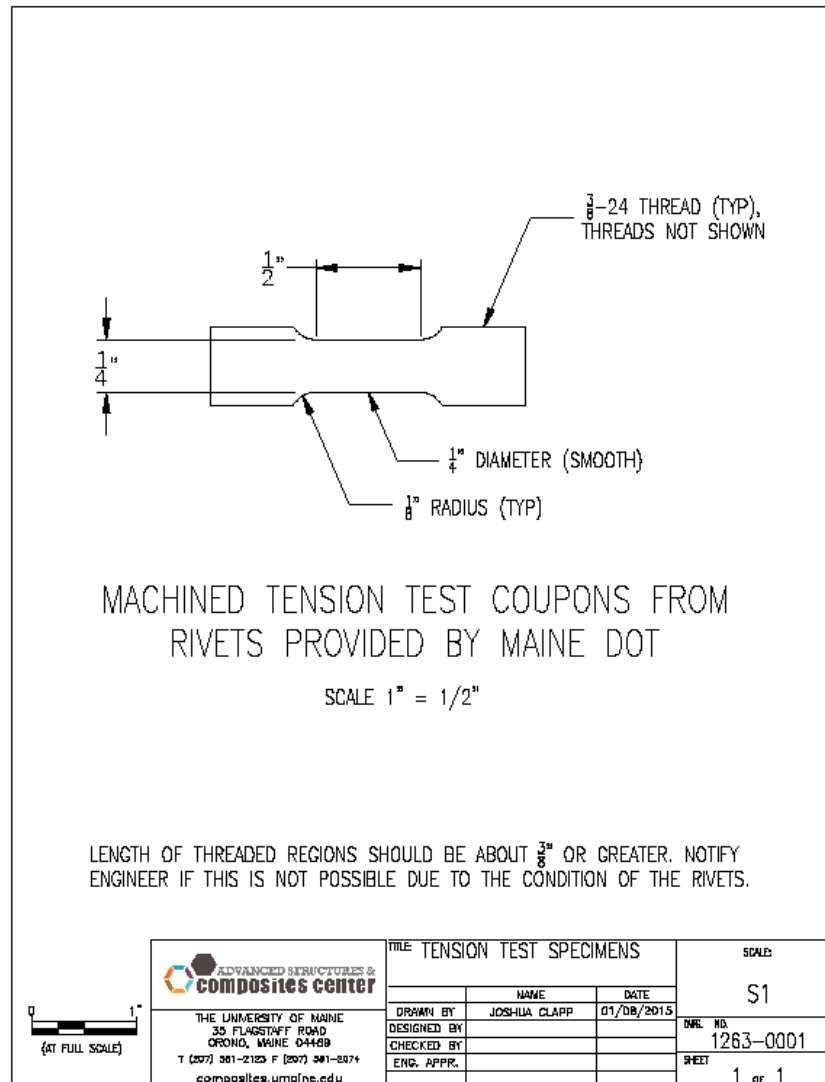


Figure 1: Machined rivet dimensional drawing



Figure 2: Typical machined rivet

Specimens were dimensioned at the UMaine Advanced Structures and Composites Center taking: diameter with three measurements at three locations along the gage length and averaging the value, and the average of three measurements of gage length. All measurement data are given in Appendix A.1, with metadata given in Table 3, measurements are given in Table 4, and calculated values are given in Table 5.

2 Testing

Testing was conducted in February 2016 at the UMaine Advanced Structures and Composites Center Mechanical Testing Laboratory using an Instron servo-hydraulic actuator (MTL #2 AS107) with a 5 kip load cell (AS601). The typical test setup is shown in Figure 3, with two internally threaded plates screwed onto the specimen, being held with hydraulic grips at 1,900 psi. Testing was first conducted in load control for specimen #01 to #05 inclusive, with approximate engineering strain rates through yield of approximately 0.01 in/in/min and at ultimate near 0.05 to 0.06 in/in/min. ASTM E8 [2] recommends a yield strain rate of 0.015 in/in/min per 7.6.3.2 and an ultimate strain rate of 0.05 in/in/min per 7.6.4. For the rest of the specimens displacement control was used to more precisely load the specimen. The specimen 20 strain rate was an outlier with a higher strain rate due to improperly entered data in the Ramp Generator Instron control system, but since the ultimate and yield strengths derived from the test were not outliers the data from that specimen is included. All of the specimen strain rate plots are shown in Appendix A.5.



Figure 3: Typical rivet testing setup

A typical specimen failure is shown in Figure 4, with well-defined necking and failure in the gage portion.



Figure 4: Typical rivet specimen after failure

3 Data Analysis

Data was recorded from the DAX software at a rate of 0.01 kHz. All load vs. position data is given in Section A.2. A typical load vs. position plot is provided in Figure 5 showing position of the crosshead (in) on the horizontal axis and the load (lbf) on the vertical axis.

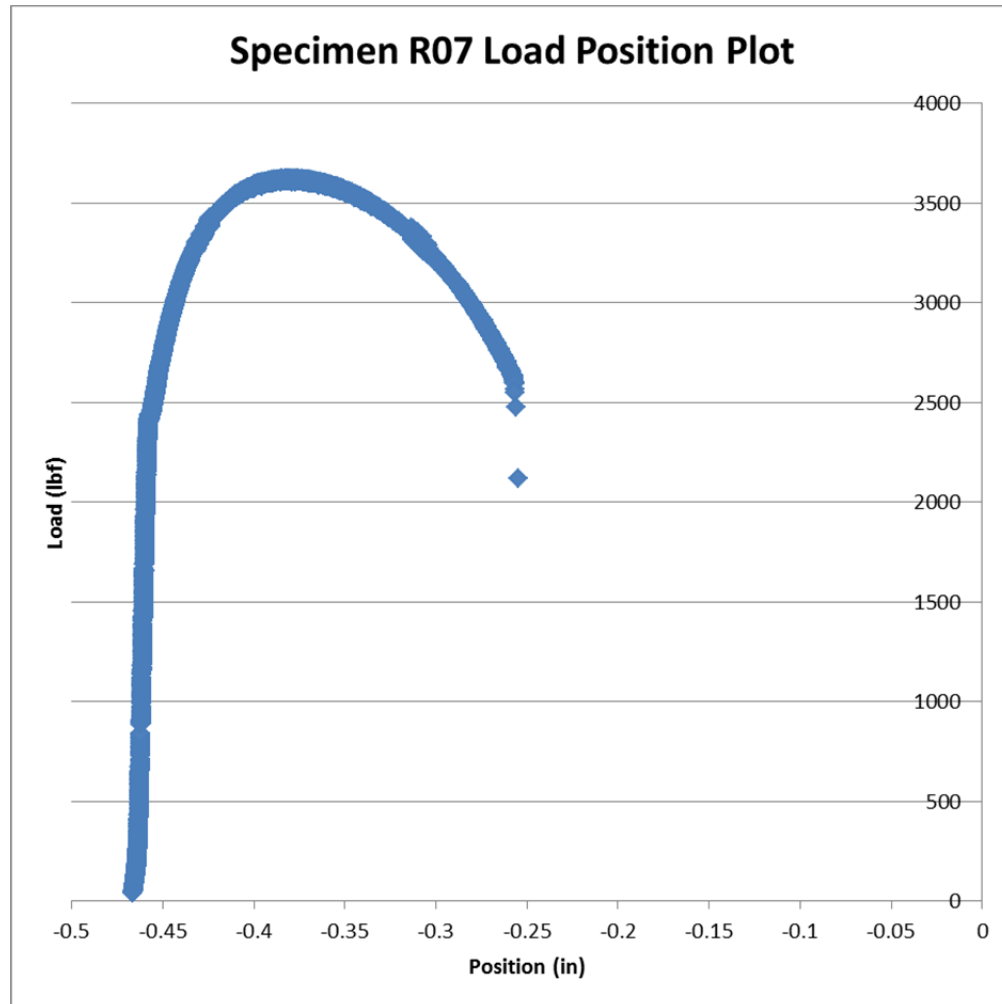


Figure 5: Typical load vs. position plot

Engineering stress (ksi) was calculated as the load divided by the original cross sectional area. Approximate engineering strain (in/in) is calculated as the change in displacement of the Instron cross-head from initial location divided by the gage length. Plots of the horizontal axis approximate engineering strain (in/in) vs. vertical axis engineering stress (ksi) are provided in Appendix A.3, and a typical stress vs. strain plot is shown in Figure 6.

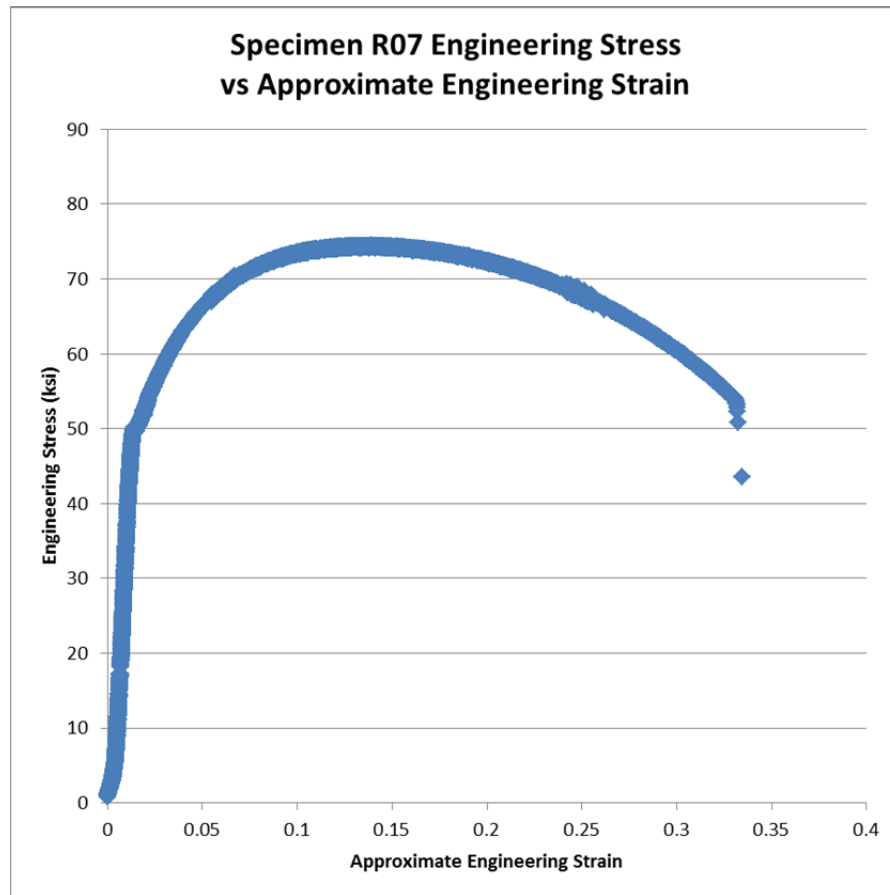


Figure 6: Typical engineering stress vs. approximate engineering strain

Yield strength was calculated using the 0.2% offset method. The vertical axis load (lbf) vs horizontal axis displacement (in) curve was plotted, in blue, and the linear portion of the curve, points considered in red, was fit with a best fit least squares regression linear fit in excel, shown as a green line. The best fit curve was then offset by 0.2% strain, shown as a red line, and the intersection with the load vs. displacement curve 5 point moving average was found, shown as a black asterisk. The equation and R^2 value for the curve fit of the linear portion of the load vs. displacement is shown on each plot. All yield plots are shown in Appendix A.4, and a typical yield plot is shown in Figure 7.

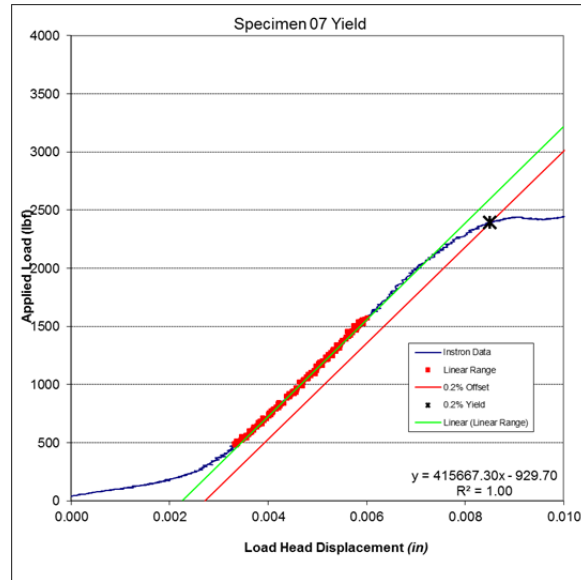


Figure 7: Typical yield curve

Strain rate was calculated for each specimen to verify compliance with standard strain rate at yield and failure requirements as described above. A typical horizontal axis engineering stress (ksi) vs. vertical axis strain rate (in/in/min) plot is shown in Figure 8, and all strain rate plots are provided in Appendix A.5.

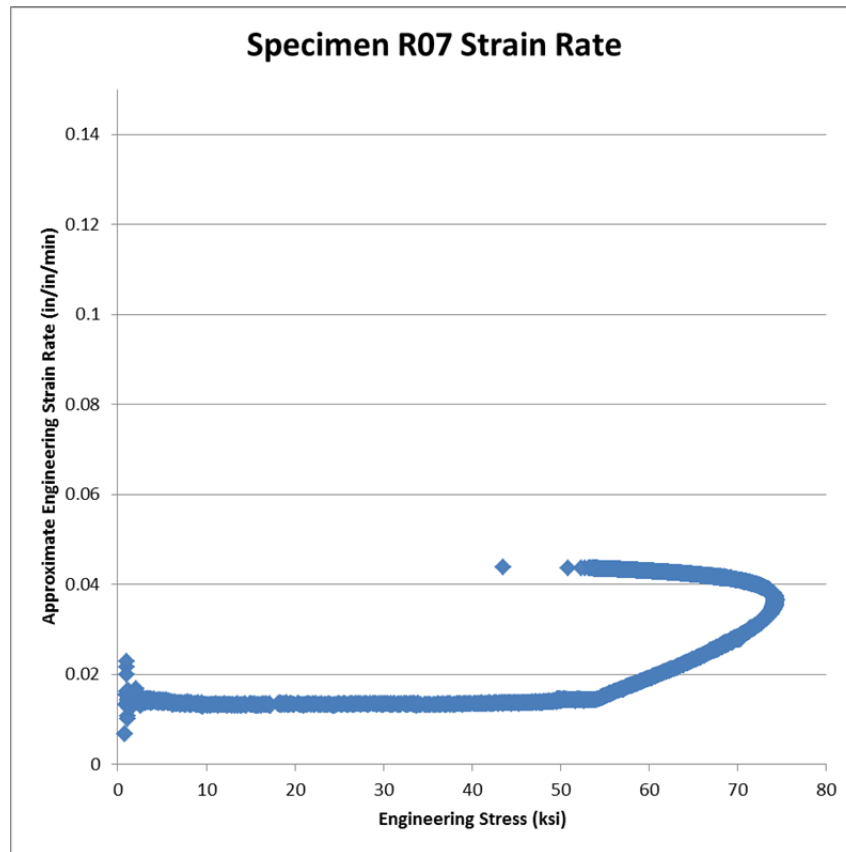


Figure 8: Typical strain rate plot

4 Detailed Test Results

Detailed results for each specimen are summarized in Table 4.

Table 2: Specimen test results

Specimen		F_y Yield Engineering Stress (ksi)	Ultimate Load (lbf)	F_u Ultimate Engineering Stress (ksi)
Type	Number	(0.2% Offset)	DAX	DAX
R	01	46.4	3228	65.7
R	02	47.3	3607	72.9
R	03	47.0	3565	72.4
R	04	44.0	3457	70.6
R	05	52.4	3848	80.1
R	06	44.9	3253	69.0
R	07	49.1	3621	74.4
R	08	45.6	3317	69.9
R	09	44.0	3200	69.1
R	10	51.2	3429	71.9
R	11	44.5	3295	67.5
R	12	40.7	3062	63.5
R	13	43.9	3172	65.2
R	14	52.3	3242	70.0
R	15	37.3	3059	63.0
R	16	39.9	3097	63.4
R	17	45.2	3197	64.5
R	18	47.6	3550	74.4
R	19	47.3	3796	76.6
R	20	46.7	3002	63.9
R	21	0.4	3217	69.0
R	22	45.6	3658	75.8
R	23	42.7	3269	69.2
	Mean	43.7	3354	69.6
	Std. Dev.	9.91	236	4.60
	COV	22.7%	7.03%	6.60%

Appendices

A.1 Specimen Dimensions

Table 3: Specimen measurement information

Specimen		Measurement Data			
Type	Number	Micrometer	Measurer	Date	Location
R	01	AS 685	Scott Tomlinson	2/2/2016 8:36	ASCC 248
R	02	AS 685	Scott Tomlinson	2/3/2016 12:00	ASCC 248
R	03	AS 685	Scott Tomlinson	2/3/2016 12:00	ASCC 248
R	04	AS 685	Scott Tomlinson	2/3/2016 12:00	ASCC 248
R	05	AS 685	Ryan Flanagan	2/5/2016 10:15	ASCC 252
R	06	AS 685	Ryan Flanagan	2/5/2016 10:15	ASCC 252
R	07	AS 685	Ryan Flanagan	2/5/2016 10:30	ASCC 252
R	08	AS 685	Ryan Flanagan	2/5/2016 10:30	ASCC 252
R	09	AS 685	Ryan Flanagan	2/5/2016 10:30	ASCC 252
R	10	AS 685	Ryan Flanagan	2/5/2016 10:30	ASCC 252
R	11	AS 685	Ryan Flanagan	2/5/2016 10:50	ASCC 252
R	12	AS 685	Ryan Flanagan	2/6/2016 10:50	ASCC 252
R	13	AS 685	Ryan Flanagan	2/5/2016 11:00	ASCC 252
R	14	AS 685	Ryan Flanagan	2/5/2016 11:05	ASCC 252
R	15	AS 685	Ryan Flanagan	2/5/2016 11:10	ASCC 252
R	16	AS 685	Ryan Flanagan	2/5/2016 11:15	ASCC 252
R	17	AS 685	Ryan Flanagan	2/5/2016 11:17	ASCC 252
R	18	AS 685	Ryan Flanagan	2/5/2016 11:20	ASCC 252
R	19	AS 685	Ryan Flanagan	2/5/2016 11:22	ASCC 252
R	20	AS 685	Ryan Flanagan	2/5/2016 11:25	ASCC 252
R	21	AS 685	Ryan Flanagan	2/5/2016 11:27	ASCC 252
R	22	AS 685	Ryan Flanagan	2/5/2016 11:30	ASCC 252
R	23	AS 685	Ryan Flanagan	2/5/2016 11:33	ASCC 252

Table 4: Specimen measurements


Specimen		Measurements in Inches											
		Top Diameter			Middle Diameter			Bottom Diameter			Gage Length		
Type	#	1	2	3	1	2	3	1	2	3	1	2	3
R	01	0.2495	0.2500	0.2490	0.2505	0.2500	0.2495	0.2510	0.2515	0.2505	0.5595	0.5790	0.5745
R	02	0.2525	0.2510	0.2510	0.2505	0.2490	0.2490	0.2540	0.2500	0.2525	0.5650	0.5525	0.5460
R	03	0.2510	0.2510	0.2510	0.2505	0.2500	0.2500	0.2510	0.2500	0.2485	0.5295	0.5325	0.5230
R	04	0.2500	0.2500	0.2495	0.2485	0.2485	0.2490	0.2510	0.2505	0.2500	0.5030	0.4995	0.5055
R	05	0.2470	0.2475	0.2475	0.2460	0.2470	0.2455	0.2480	0.2490	0.2490	0.6425	0.6670	0.6505
R	06	0.2465	0.2465	0.2470	0.2440	0.2440	0.2435	0.2455	0.2445	0.2440	0.6240	0.6285	0.6170
R	07	0.2520	0.2500	0.2500	0.2470	0.2485	0.2490	0.2475	0.2480	0.2480	0.6390	0.6350	0.6215
R	08	0.2445	0.2485	0.2455	0.2445	0.2450	0.2450	0.2460	0.2475	0.2460	0.6395	0.6360	0.6390
R	09	0.2450	0.2455	0.2445	0.2440	0.2415	0.2400	0.2405	0.2430	0.2420	0.5685	0.5700	0.5740
R	10	0.2475	0.2470	0.2465	0.2430	0.2465	0.2475	0.2465	0.2470	0.2465	0.6475	0.6685	0.6570
R	11	0.2510	0.2495	0.2495	0.2470	0.2490	0.2475	0.2500	0.2505	0.2495	0.6455	0.6440	0.6500
R	12	0.2480	0.2475	0.2480	0.2475	0.2480	0.2455	0.2485	0.2490	0.2480	0.5795	0.5830	0.5830
R	13	0.2490	0.2490	0.2490	0.2490	0.2480	0.2480	0.2495	0.2490	0.2490	0.6045	0.5995	0.6060
R	14	0.2390	0.2395	0.2380	0.2435	0.2435	0.2425	0.2465	0.2465	0.2470	0.6325	0.6325	0.6345
R	15	0.2470	0.2485	0.2470	0.2485	0.2480	0.2480	0.2510	0.2490	0.2505	0.6340	0.6365	0.6405
R	16	0.2500	0.2495	0.2490	0.2495	0.2485	0.2490	0.2500	0.2500	0.2500	0.6935	0.6895	0.6800
R	17	0.2485	0.2500	0.2485	0.2510	0.2485	0.2505	0.2545	0.2540	0.2550	0.5900	0.5970	0.5955
R	18	0.2445	0.2475	0.2455	0.2470	0.2470	0.2445	0.2480	0.2475	0.2465	0.6330	0.6270	0.6260
R	19	0.2530	0.2550	0.2535	0.2510	0.2505	0.2510	0.2490	0.2485	0.2495	0.6055	0.6045	0.6050
R	20	0.2435	0.2470	0.2460	0.2445	0.2435	0.2445	0.2445	0.2435	0.2440	0.5855	0.5775	0.5770
R	21	0.2445	0.2465	0.2440	0.2425	0.2415	0.2440	0.2435	0.2435	0.2435	0.6345	0.6265	0.6340
R	22	0.2475	0.2480	0.2475	0.2465	0.2470	0.2470	0.2495	0.2500	0.2480	0.6110	0.6190	0.6255
R	23	0.2445	0.2445	0.2455	0.2445	0.2445	0.2455	0.2470	0.2460	0.2460	0.6390	0.6240	0.6170


Table 5: Calculated specimen dimensions


Specimen		Area	Measurements (in)									COV (%)			
			Diameter	Mean				Std. Dev.							
Type	#	In ²			Top	Middle	Bottom	Gage	Top	Middle	Bottom	Gage	Top	Middle	Bottom
R	01	0.0492	0.2502	0.5341	0.2500	0.2510	0.5710	0.0004	0.0004	0.0004	0.0083	0.08	0.16	0.16	1.46
R	02	0.0495	0.2511	0.5569	0.2495	0.2522	0.5545	0.0007	0.0007	0.0016	0.0079	0.13	0.28	0.65	1.42
R	03	0.0492	0.2503	0.5519	0.2502	0.2498	0.5283	0.0000	0.0002	0.0010	0.0040	0.00	0.09	0.41	0.75
R	04	0.0490	0.2497	0.5459	0.2487	0.2505	0.5027	0.0002	0.0002	0.0004	0.0025	0.04	0.09	0.16	0.49
R	05	0.0481	0.2474	0.5752	0.2462	0.2487	0.6533	0.0002	0.0006	0.0005	0.0102	0.04	0.25	0.19	1.56
R	06	0.0472	0.2451	0.5698	0.2438	0.2447	0.6232	0.0002	0.0002	0.0006	0.0047	0.04	0.10	0.25	0.76
R	07	0.0487	0.2489	0.5734	0.2482	0.2478	0.6318	0.0009	0.0008	0.0002	0.0075	0.16	0.34	0.10	1.18
R	08	0.0475	0.2458	0.5741	0.2448	0.2465	0.6382	0.0017	0.0002	0.0007	0.0015	0.30	0.10	0.29	0.24
R	09	0.0463	0.2429	0.5598	0.2418	0.2418	0.5708	0.0004	0.0016	0.0010	0.0023	0.07	0.68	0.42	0.41
R	10	0.0477	0.2464	0.5778	0.2457	0.2467	0.6577	0.0004	0.0019	0.0002	0.0086	0.07	0.79	0.10	1.31
R	11	0.0488	0.2493	0.5769	0.2478	0.2500	0.6465	0.0007	0.0008	0.0004	0.0025	0.12	0.34	0.16	0.39
R	12	0.0482	0.2478	0.5625	0.2470	0.2485	0.5818	0.0002	0.0011	0.0004	0.0016	0.04	0.44	0.16	0.28
R	13	0.0486	0.2488	0.5686	0.2483	0.2492	0.6033	0.0000	0.0005	0.0002	0.0028	0.00	0.19	0.09	0.46
R	14	0.0463	0.2429	0.5703	0.2432	0.2467	0.6332	0.0006	0.0005	0.0002	0.0009	0.11	0.19	0.10	0.15
R	15	0.0485	0.2486	0.5743	0.2482	0.2502	0.6370	0.0007	0.0002	0.0008	0.0027	0.12	0.09	0.34	0.42
R	16	0.0489	0.2495	0.5750	0.2490	0.2500	0.6877	0.0004	0.0004	0.0000	0.0057	0.07	0.16	0.00	0.82
R	17	0.0495	0.2512	0.5674	0.2500	0.2545	0.5942	0.0007	0.0011	0.0004	0.0030	0.12	0.43	0.16	0.51
R	18	0.0477	0.2464	0.5707	0.2462	0.2473	0.6287	0.0012	0.0012	0.0006	0.0031	0.22	0.48	0.25	0.49
R	19	0.0496	0.2512	0.5688	0.2508	0.2490	0.6050	0.0008	0.0002	0.0004	0.0004	0.15	0.09	0.16	0.07
R	20	0.0470	0.2446	0.5580	0.2442	0.2440	0.5800	0.0015	0.0005	0.0004	0.0039	0.26	0.19	0.17	0.67
R	21	0.0467	0.2437	0.5688	0.2427	0.2435	0.6317	0.0011	0.0010	0.0000	0.0037	0.19	0.42	0.00	0.58
R	22	0.0483	0.2479	0.5700	0.2468	0.2492	0.6185	0.0002	0.0002	0.0008	0.0059	0.04	0.10	0.34	0.96
R	23	0.0473	0.2453	0.5704	0.2448	0.2463	0.6267	0.0005	0.0005	0.0005	0.0092	0.08	0.19	0.19	1.46


A.2 Load vs. Position Plots


The load is plotted against position data obtained for each machined rivet specimen is provided in this appendix.

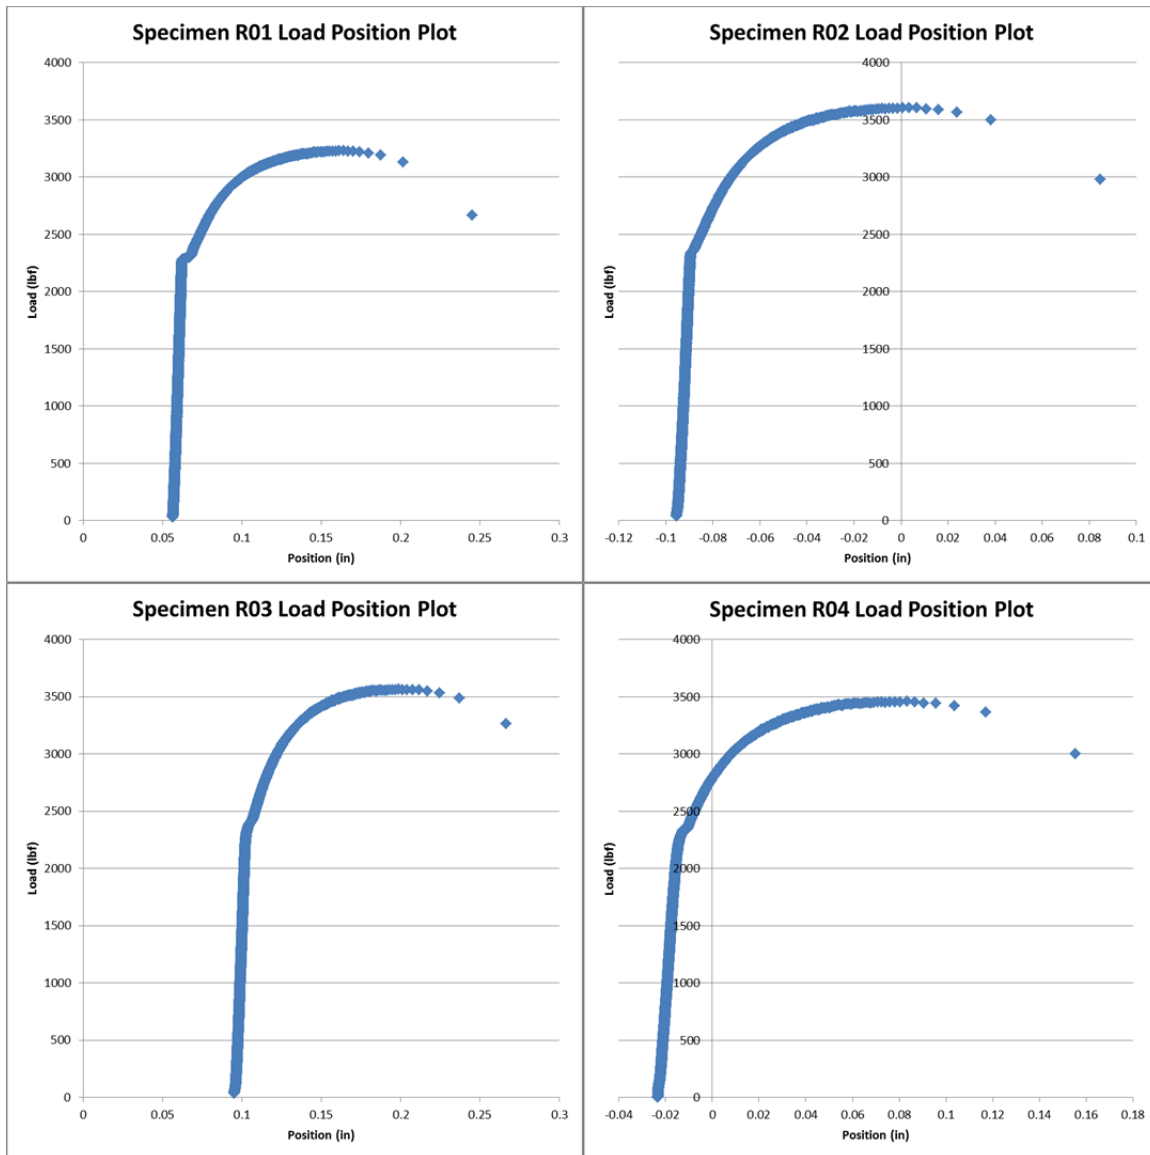

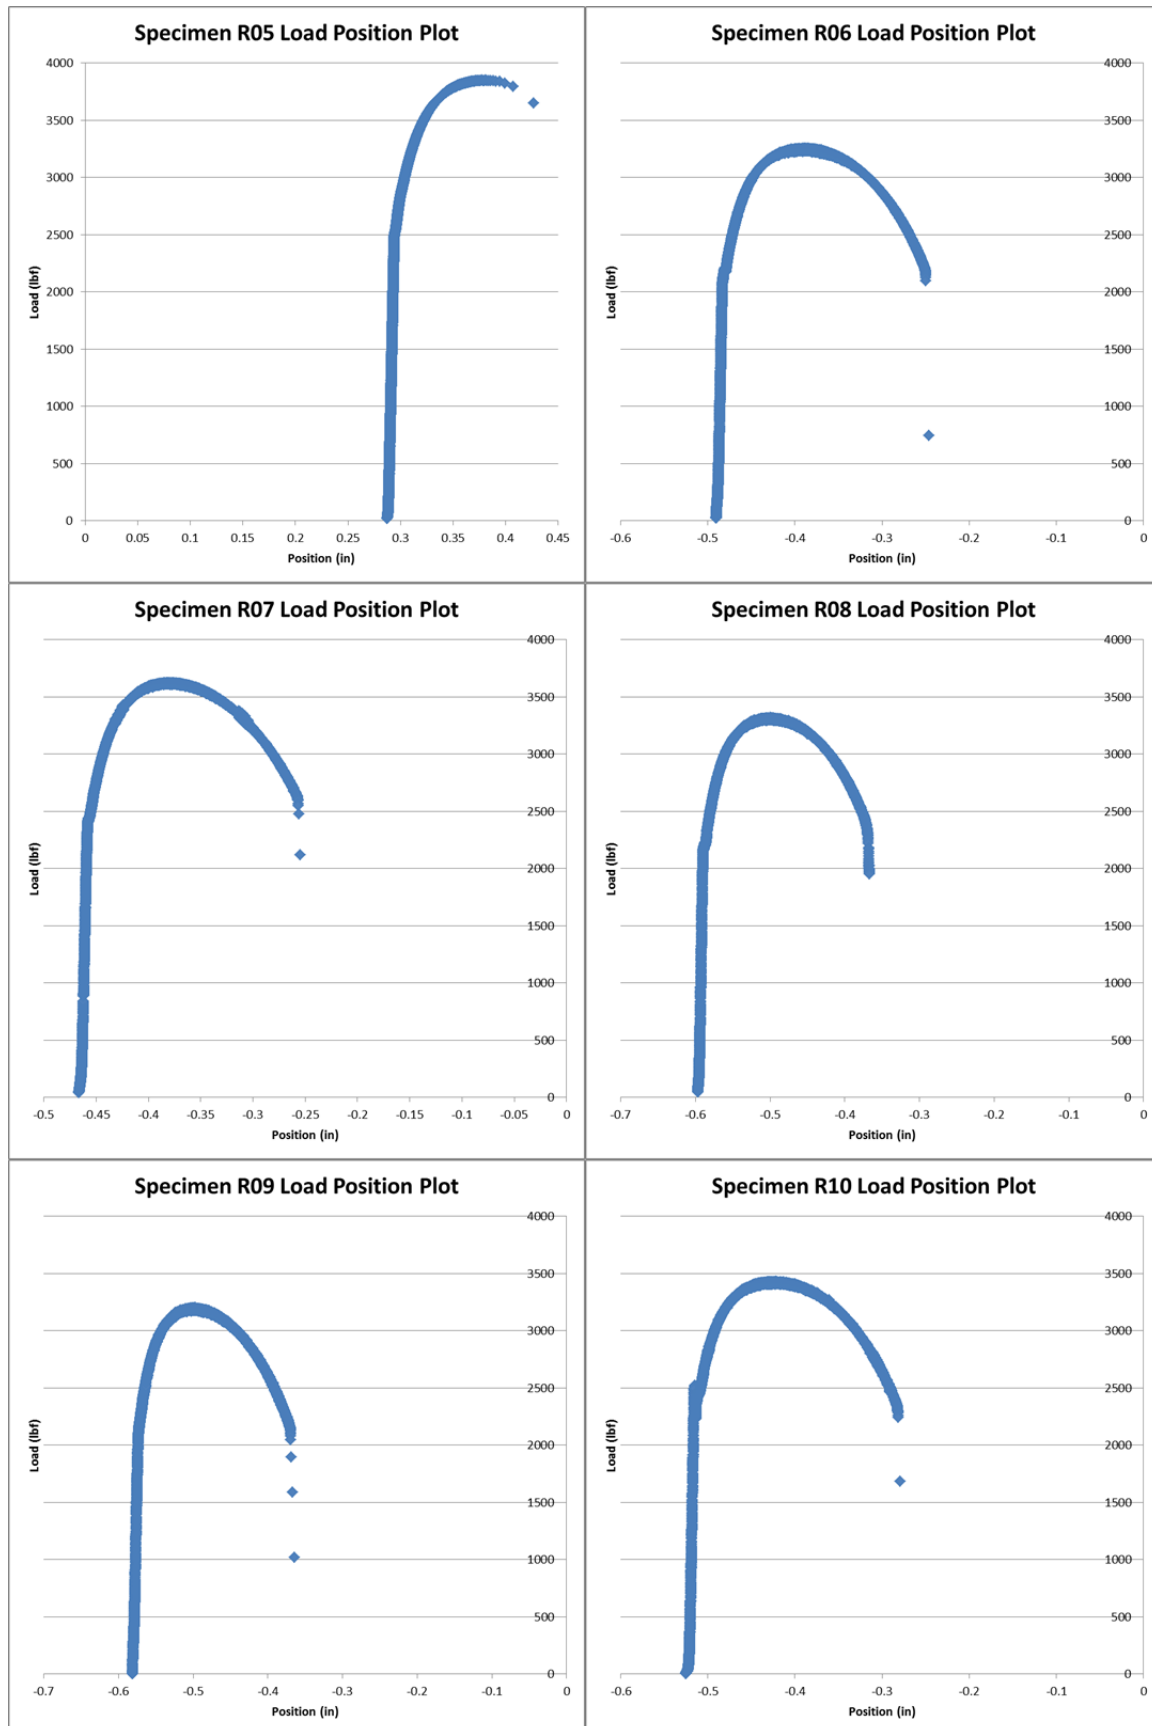

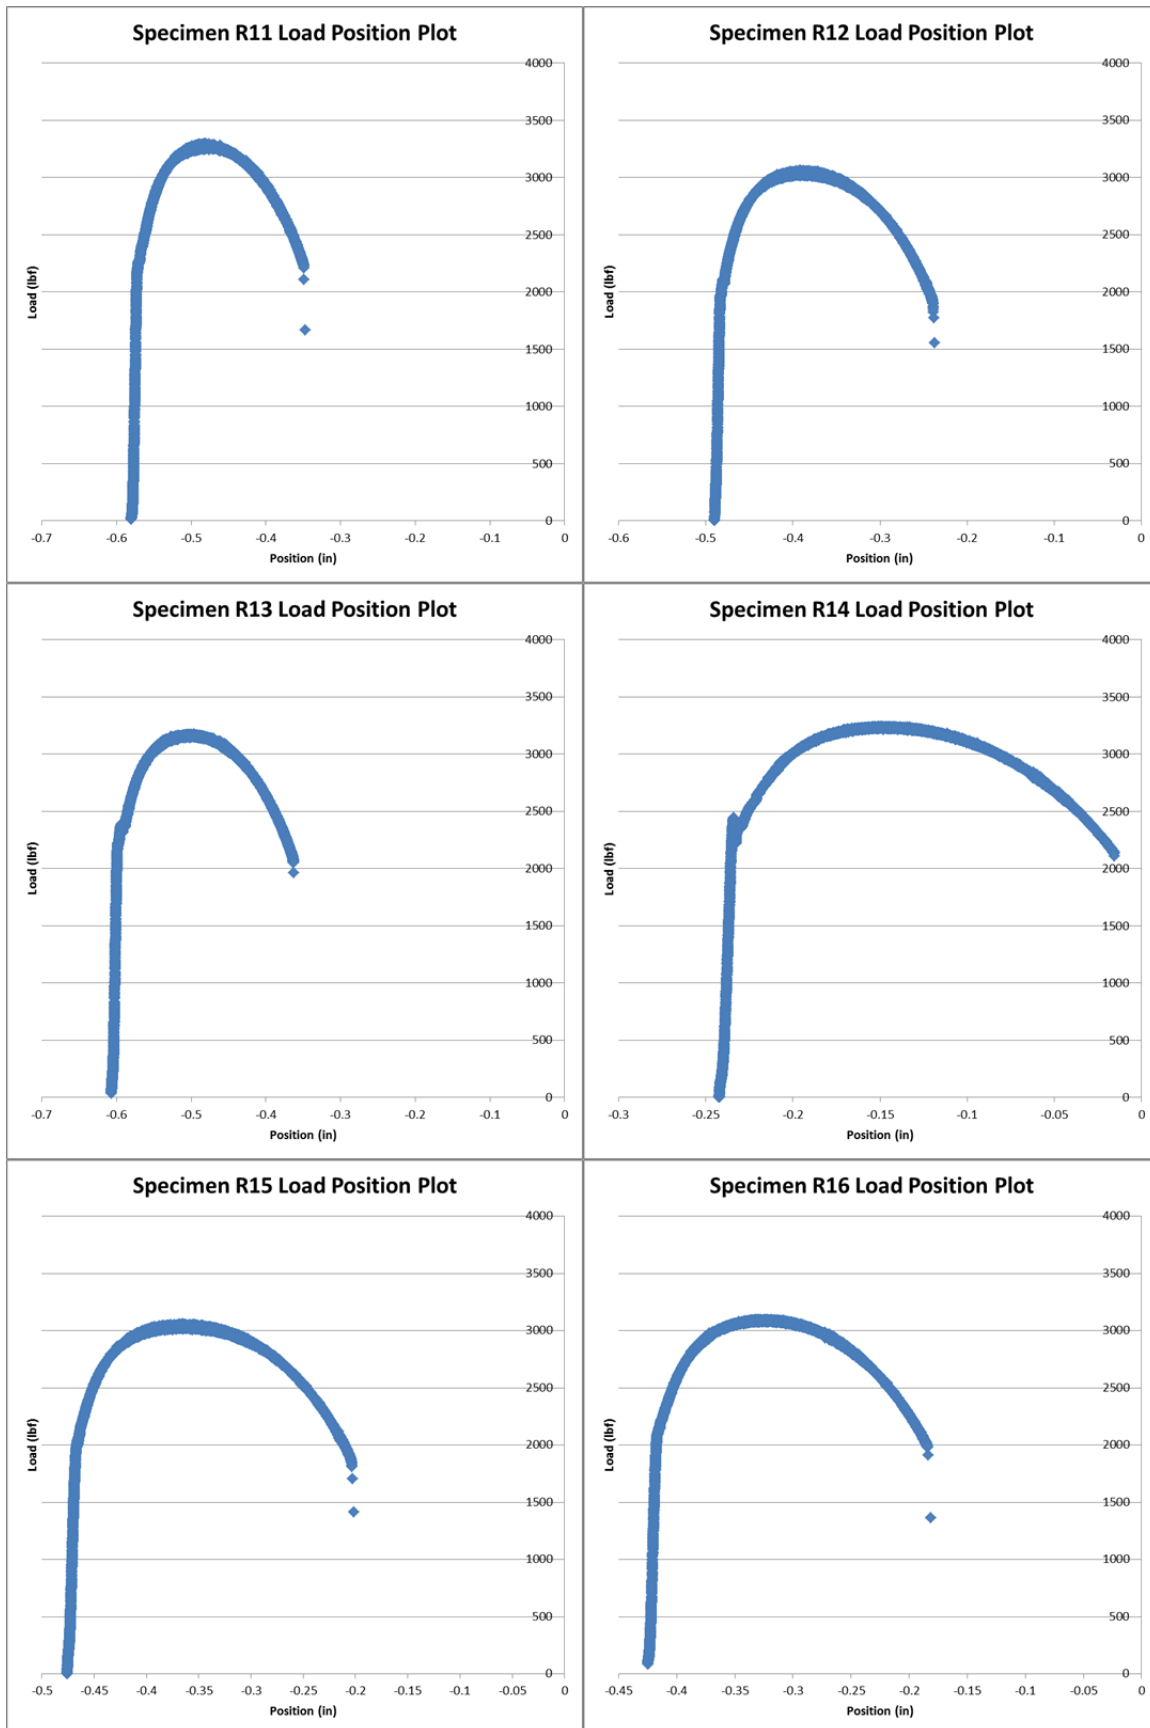


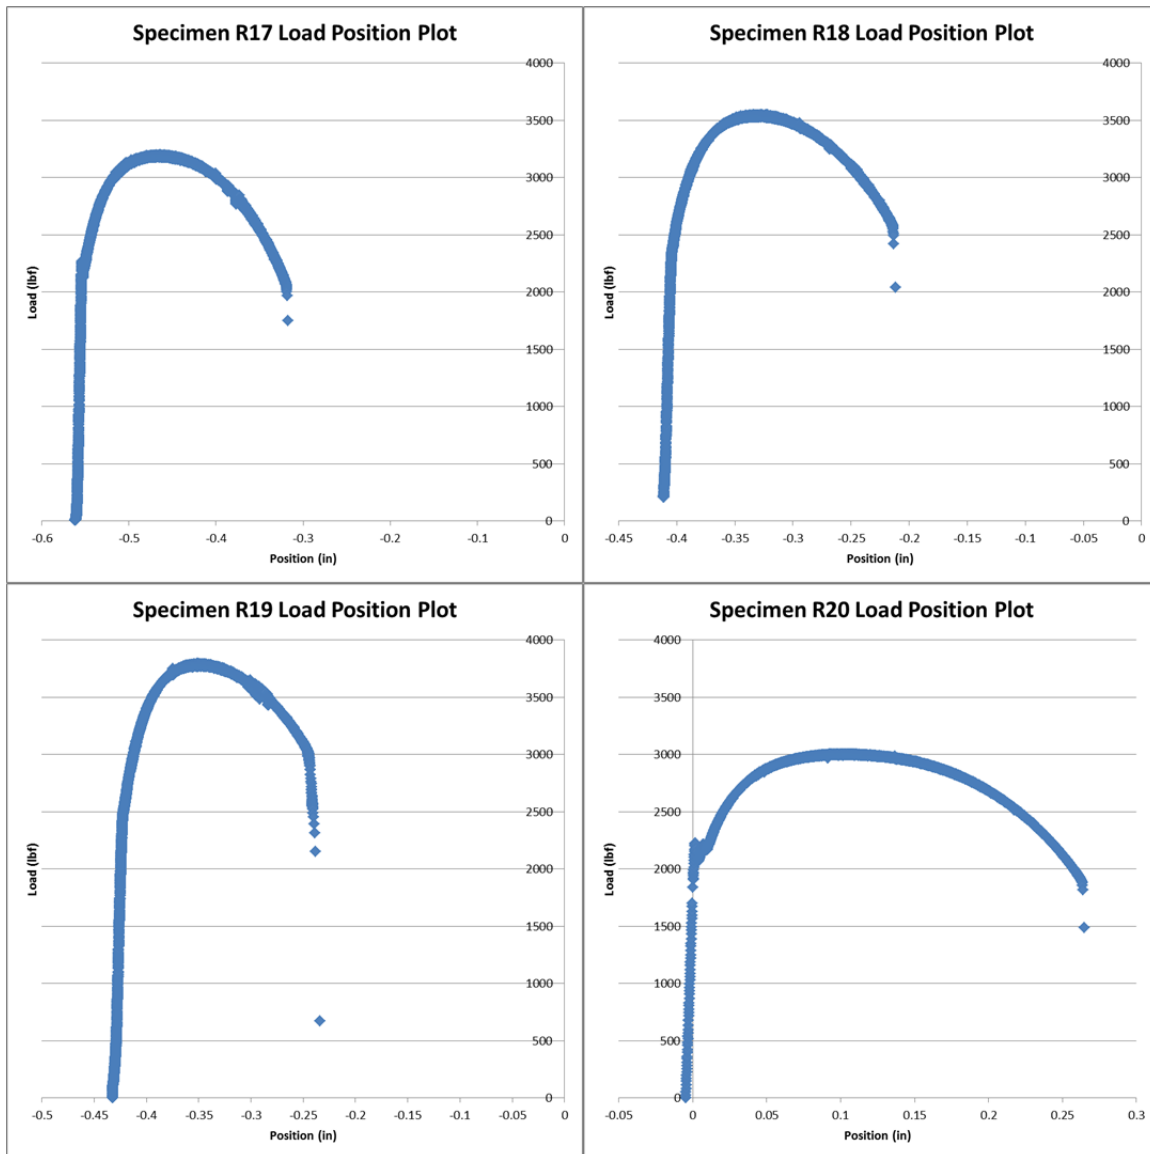


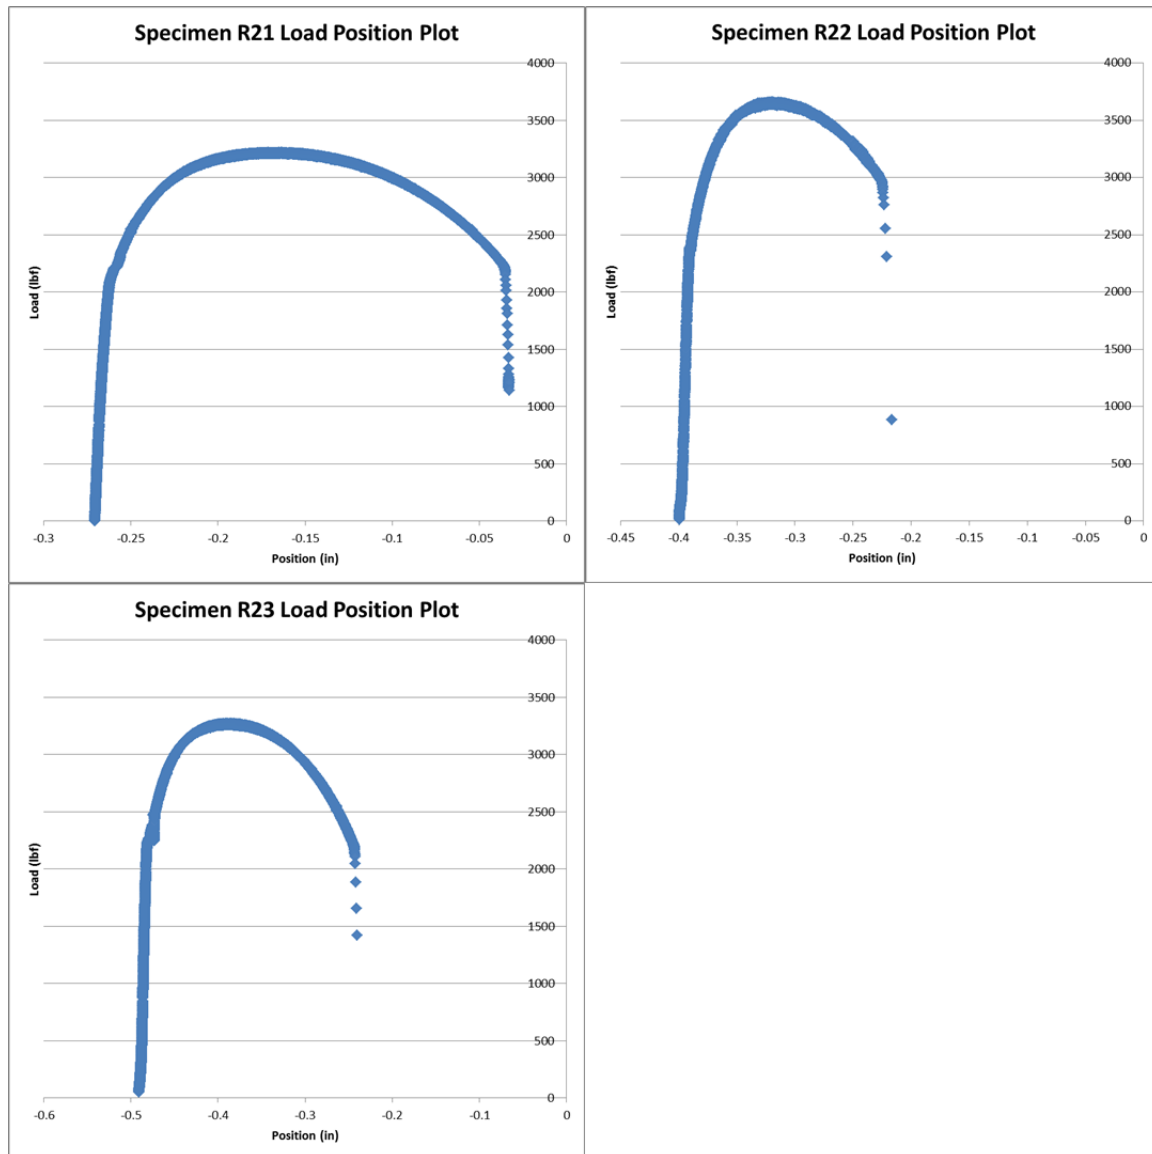



A.3 Engineering Stress vs. Approximate Engineering Strain


The engineering stress is plotted against the approximate engineering strain for each rivet specimen in this appendix.

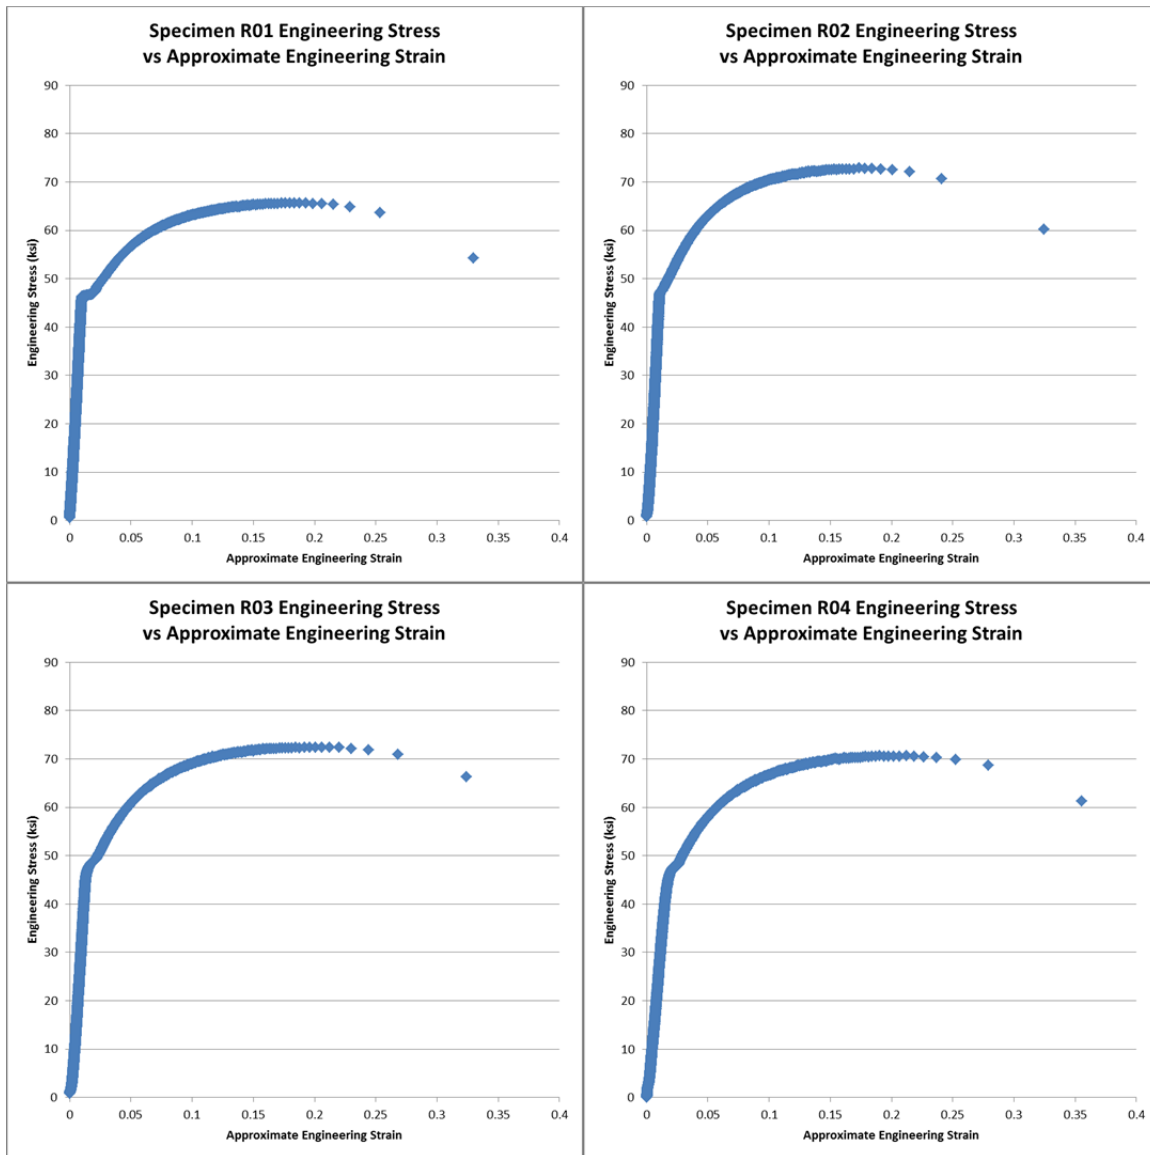

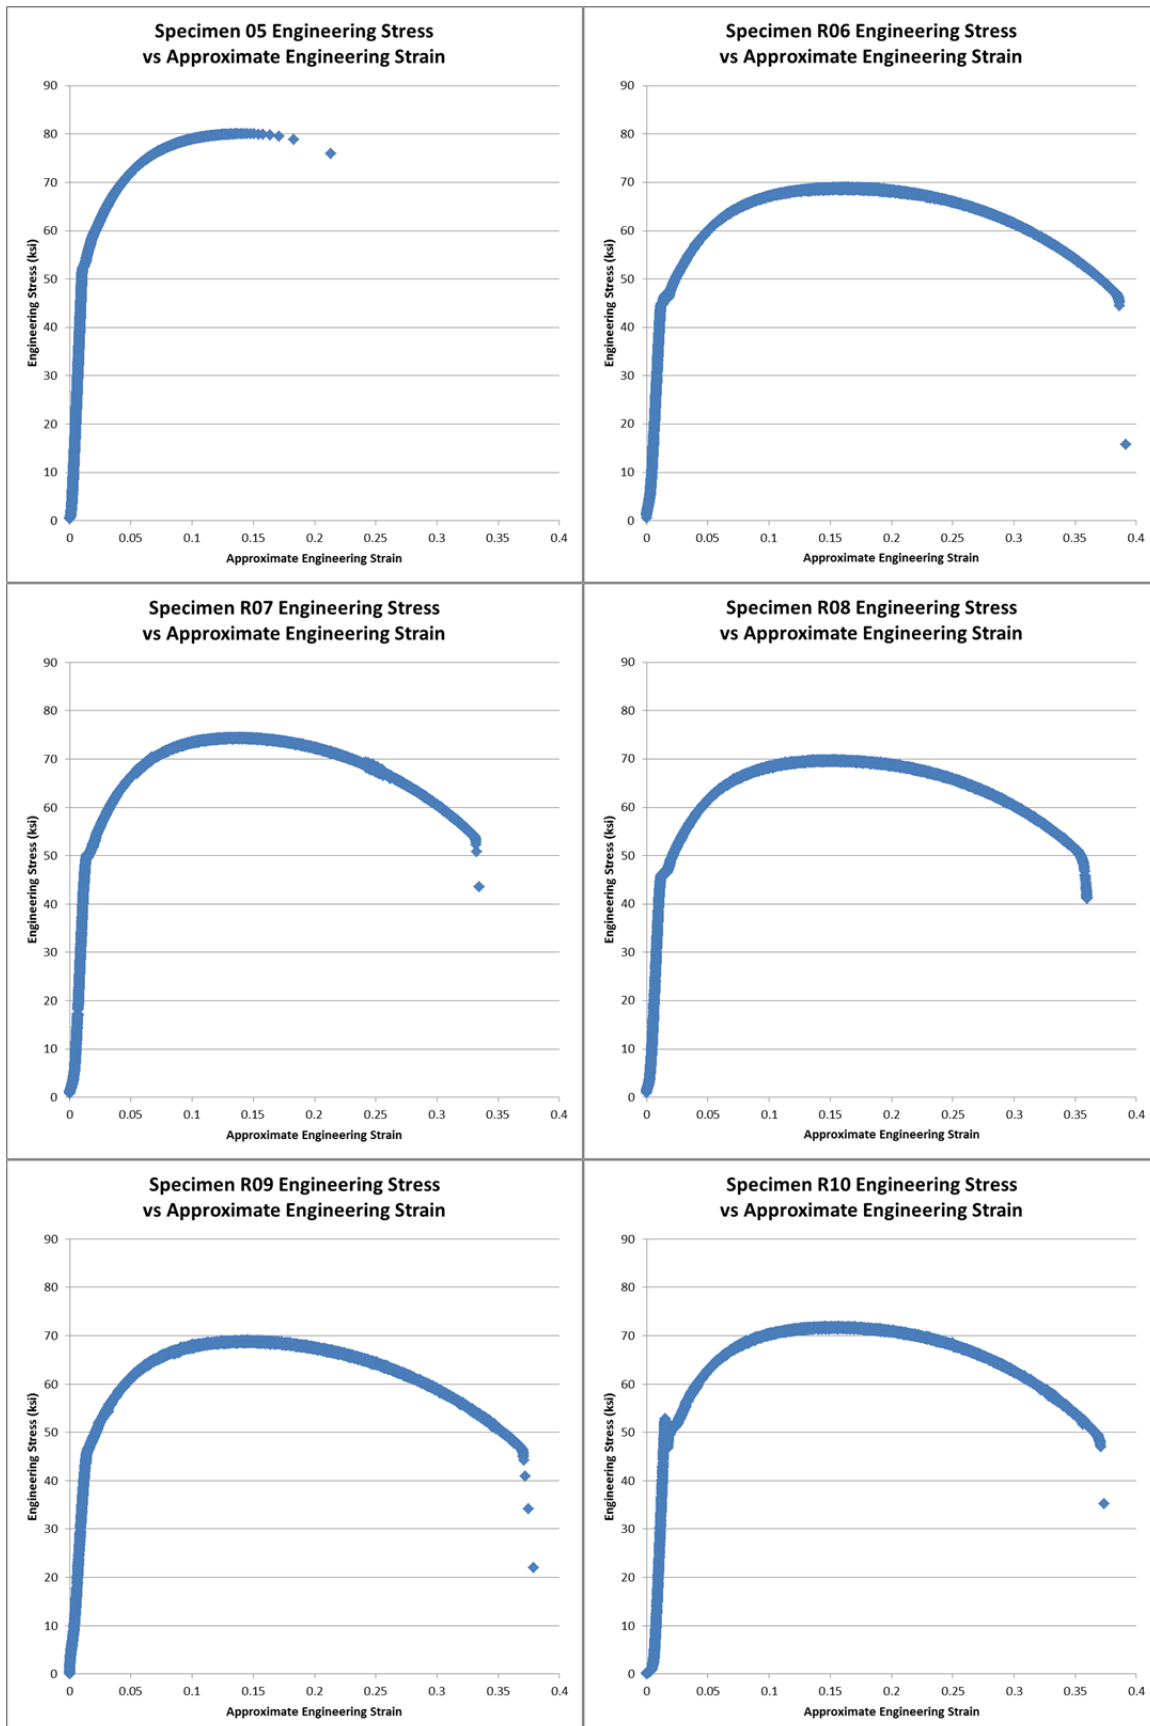

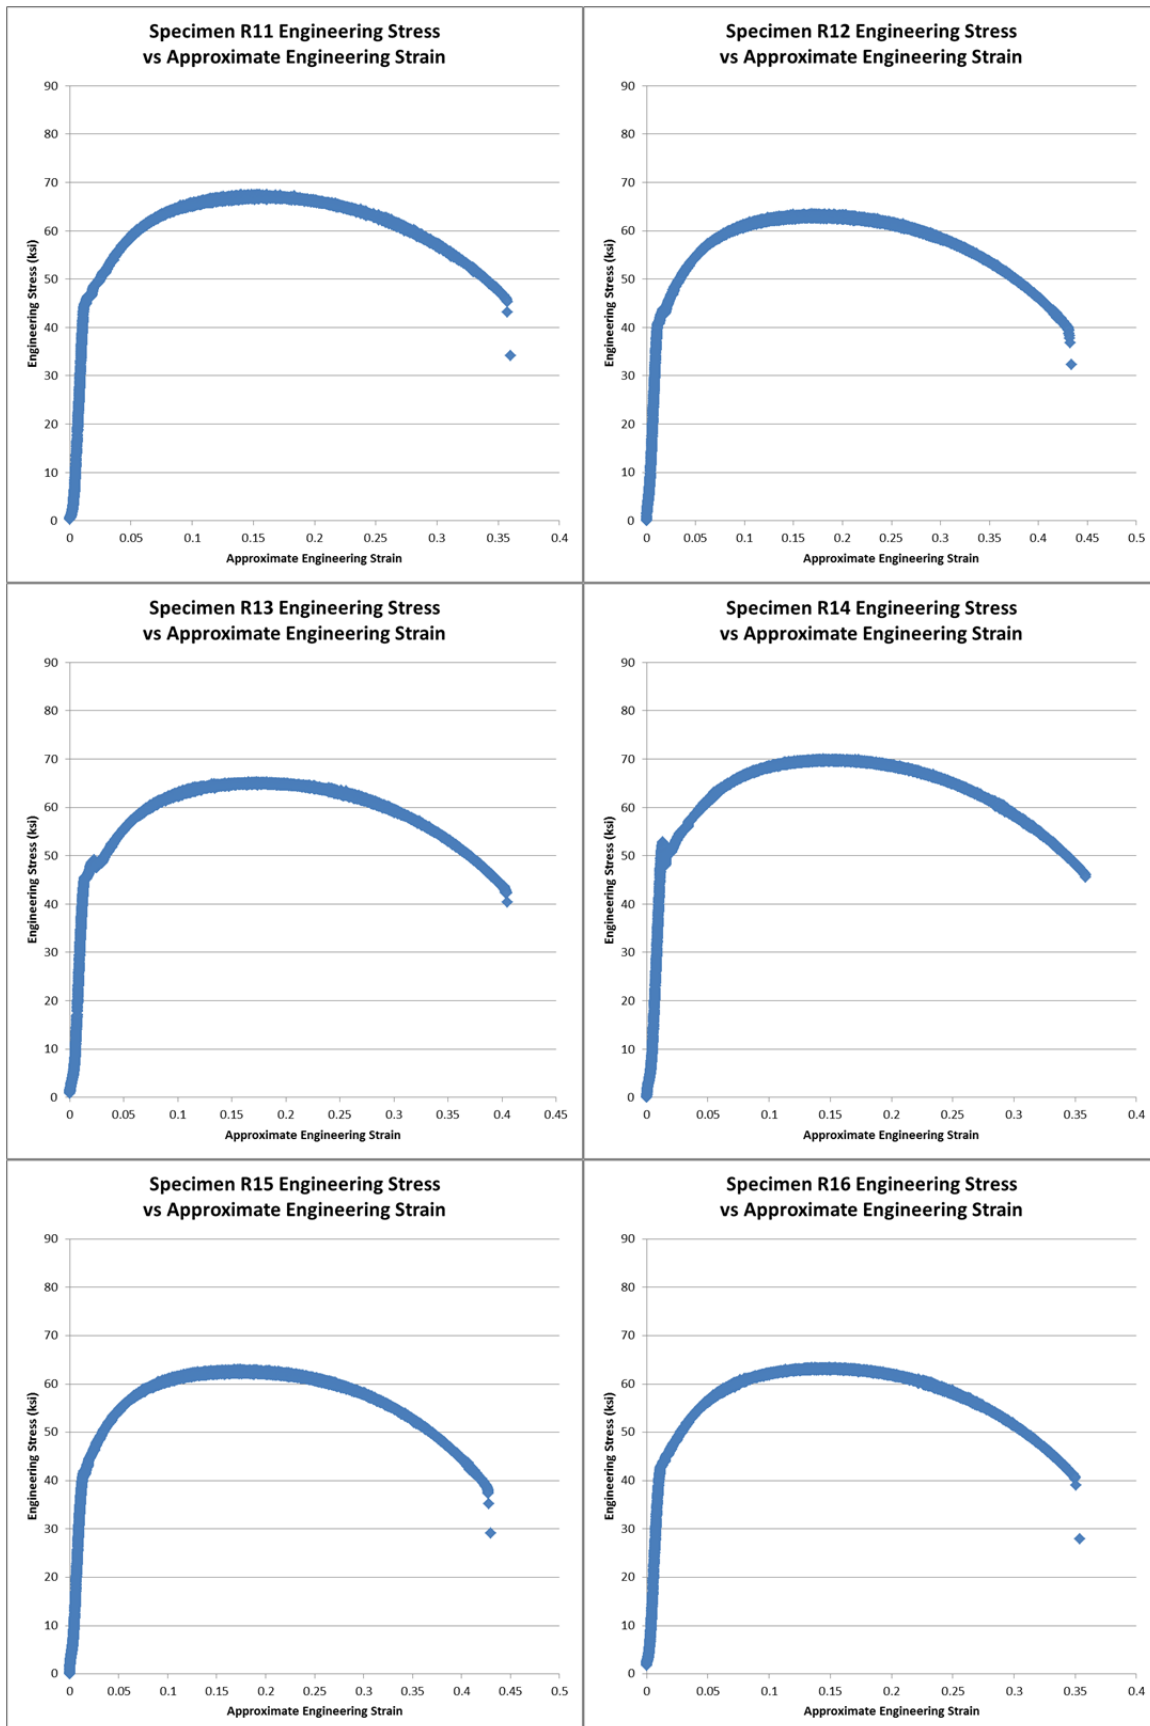


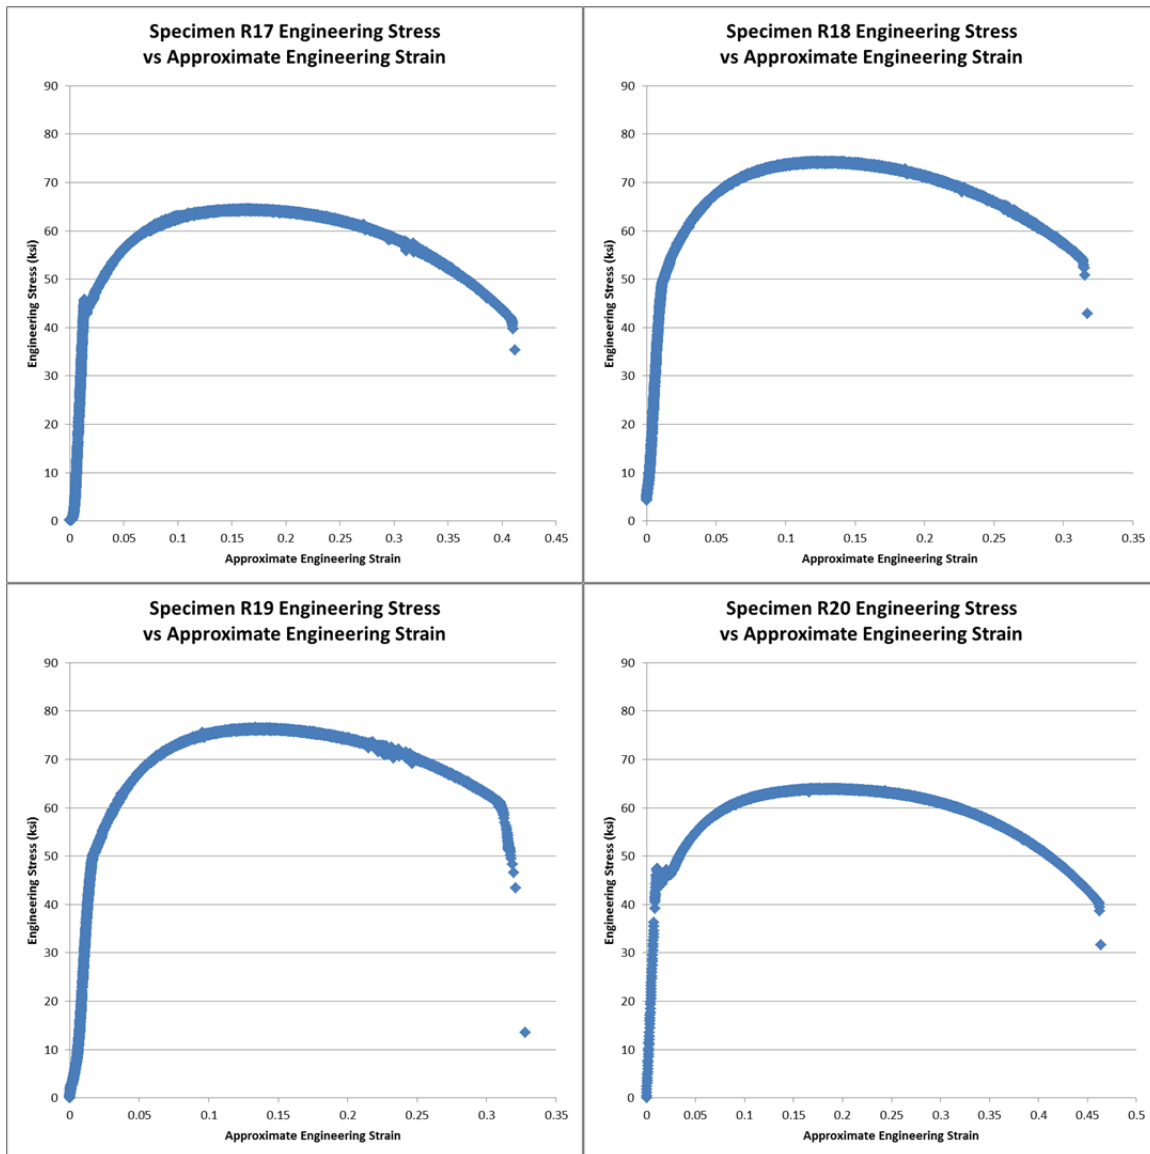


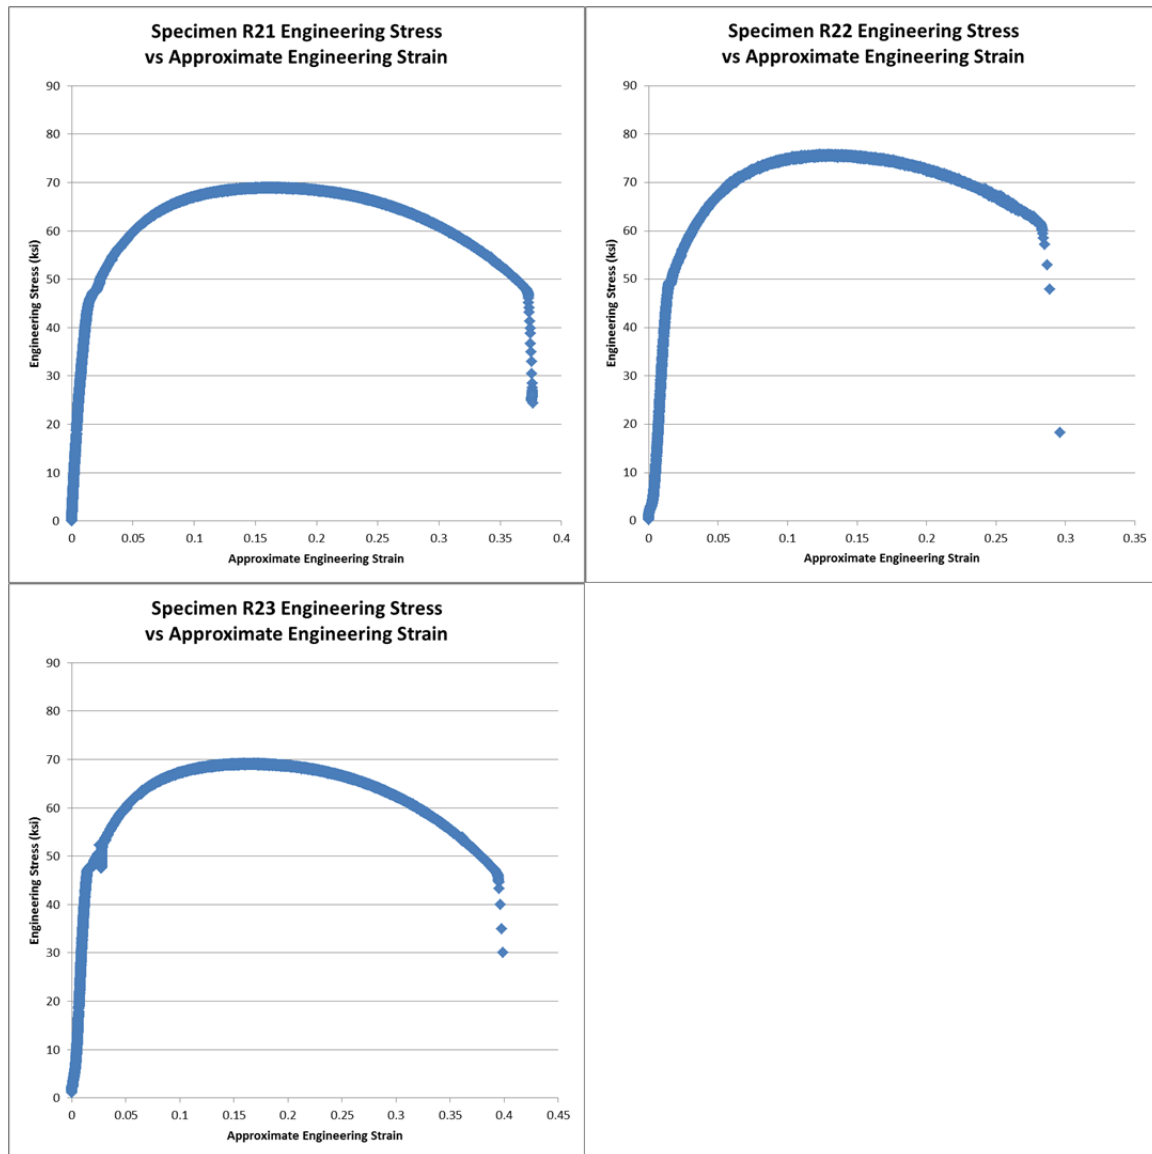



A.4 Load vs. Position Yield Strength Calculation Plots


The plots used to calculate the yield strength of each rivet specimen is provided in this appendix.

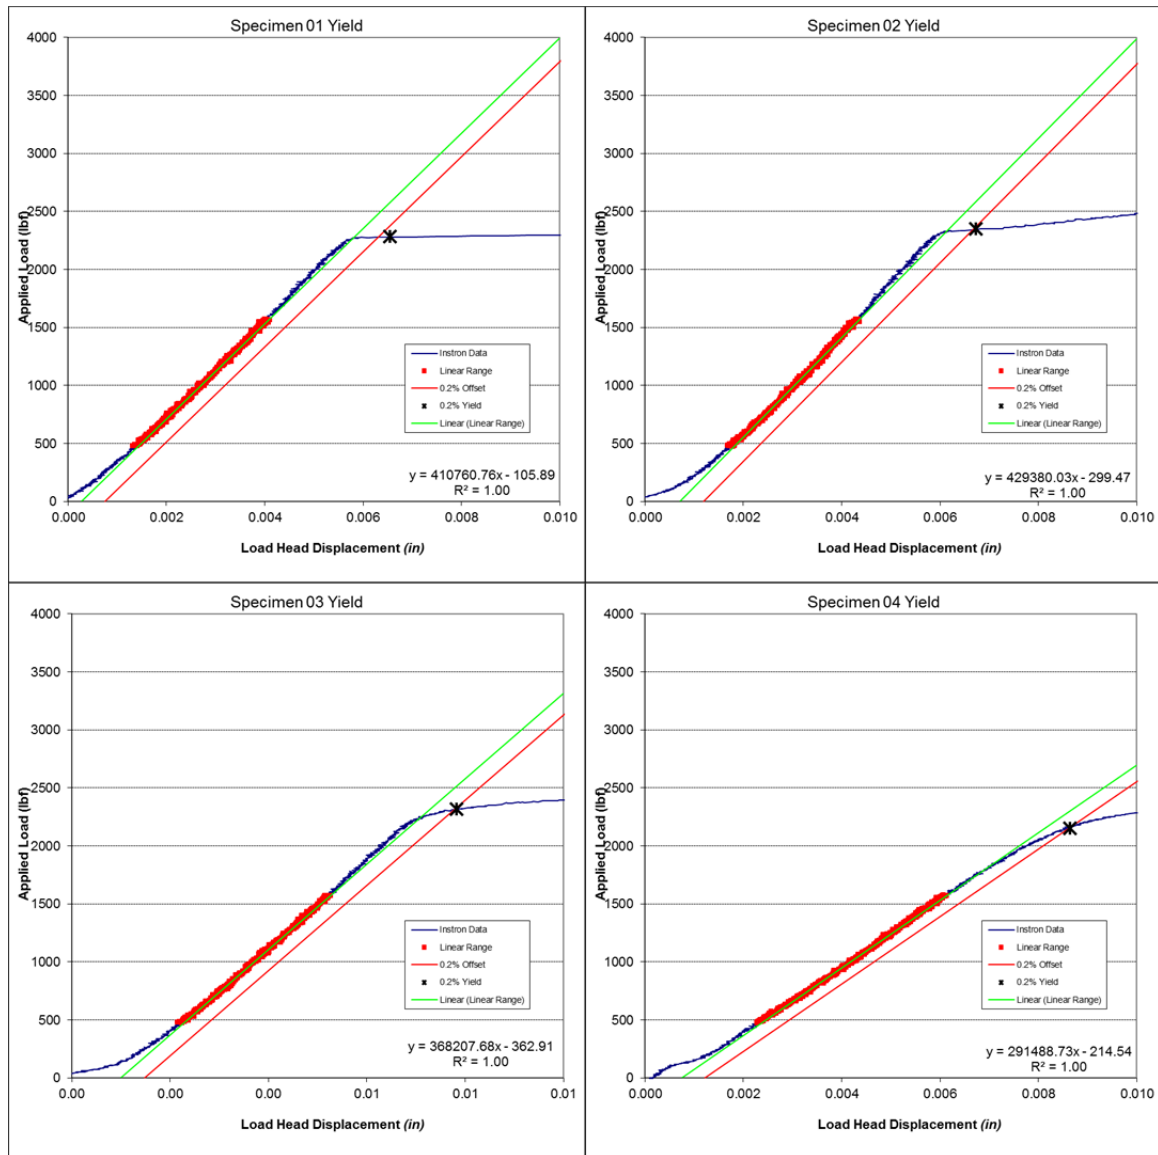

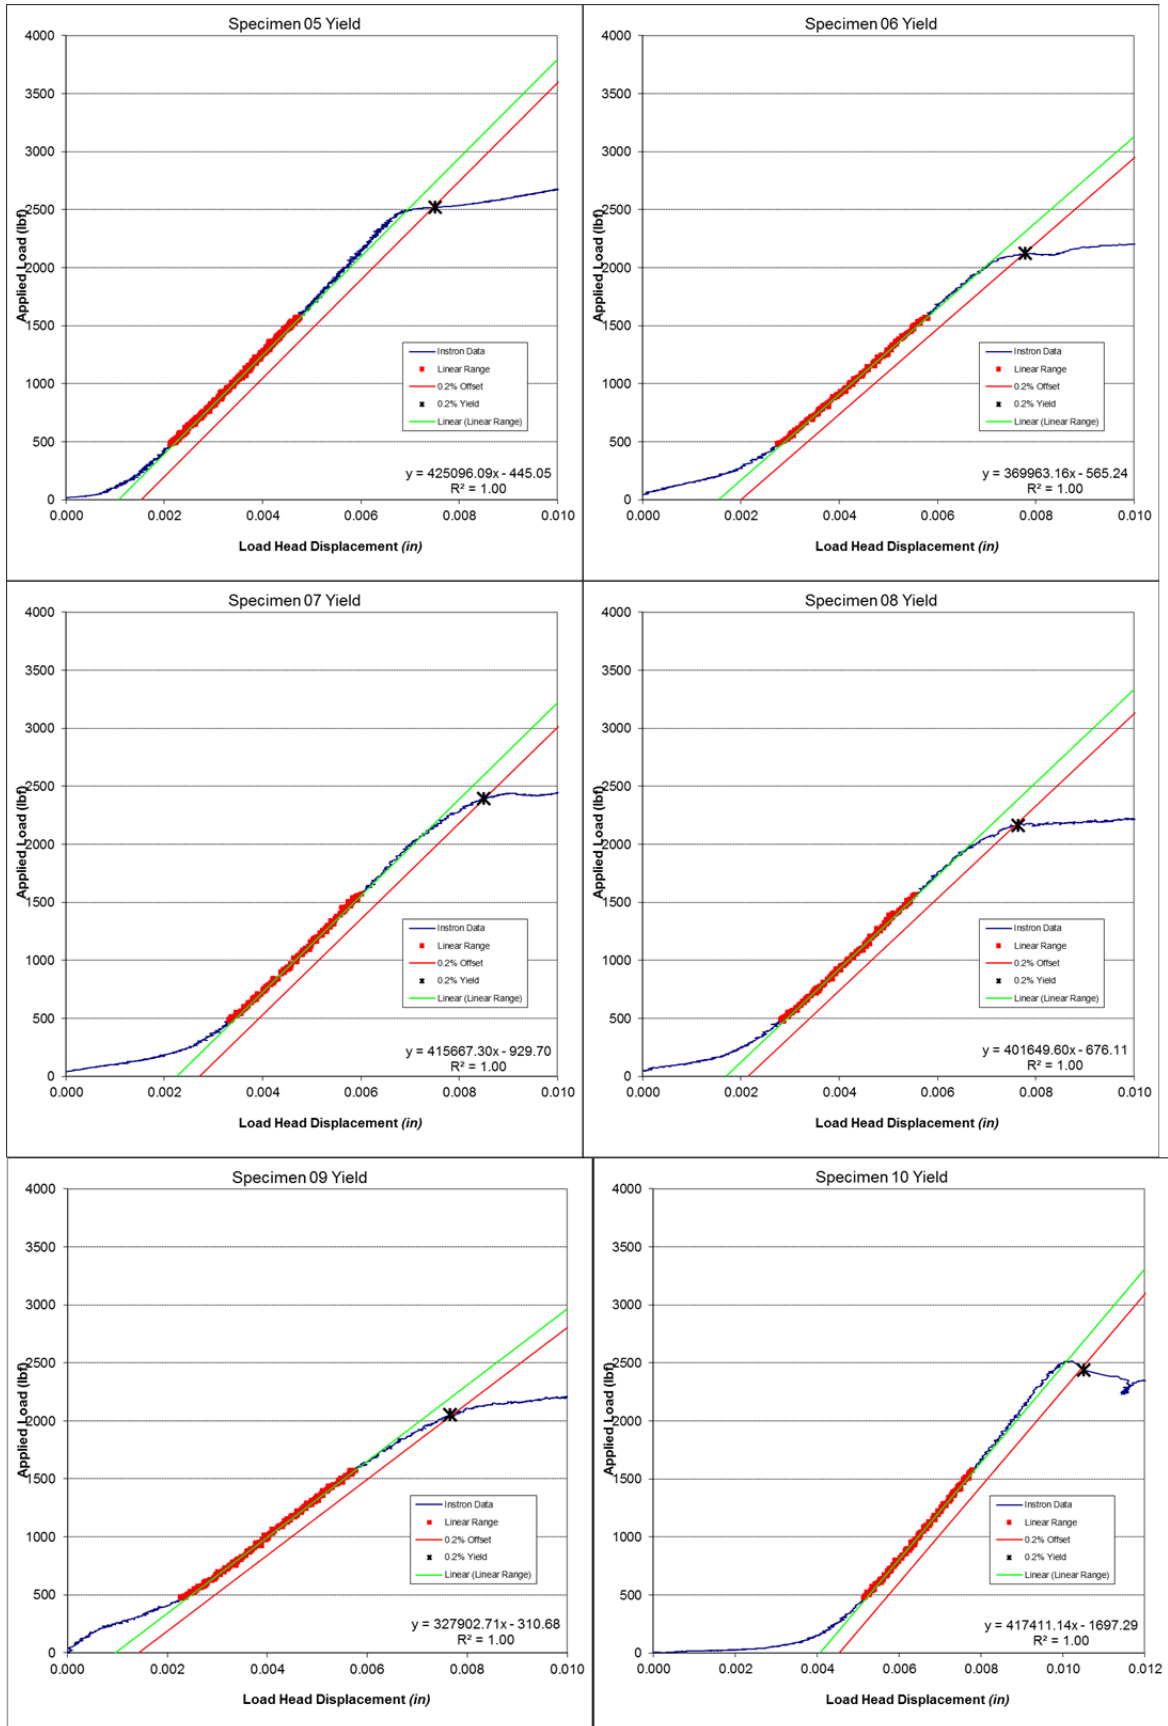

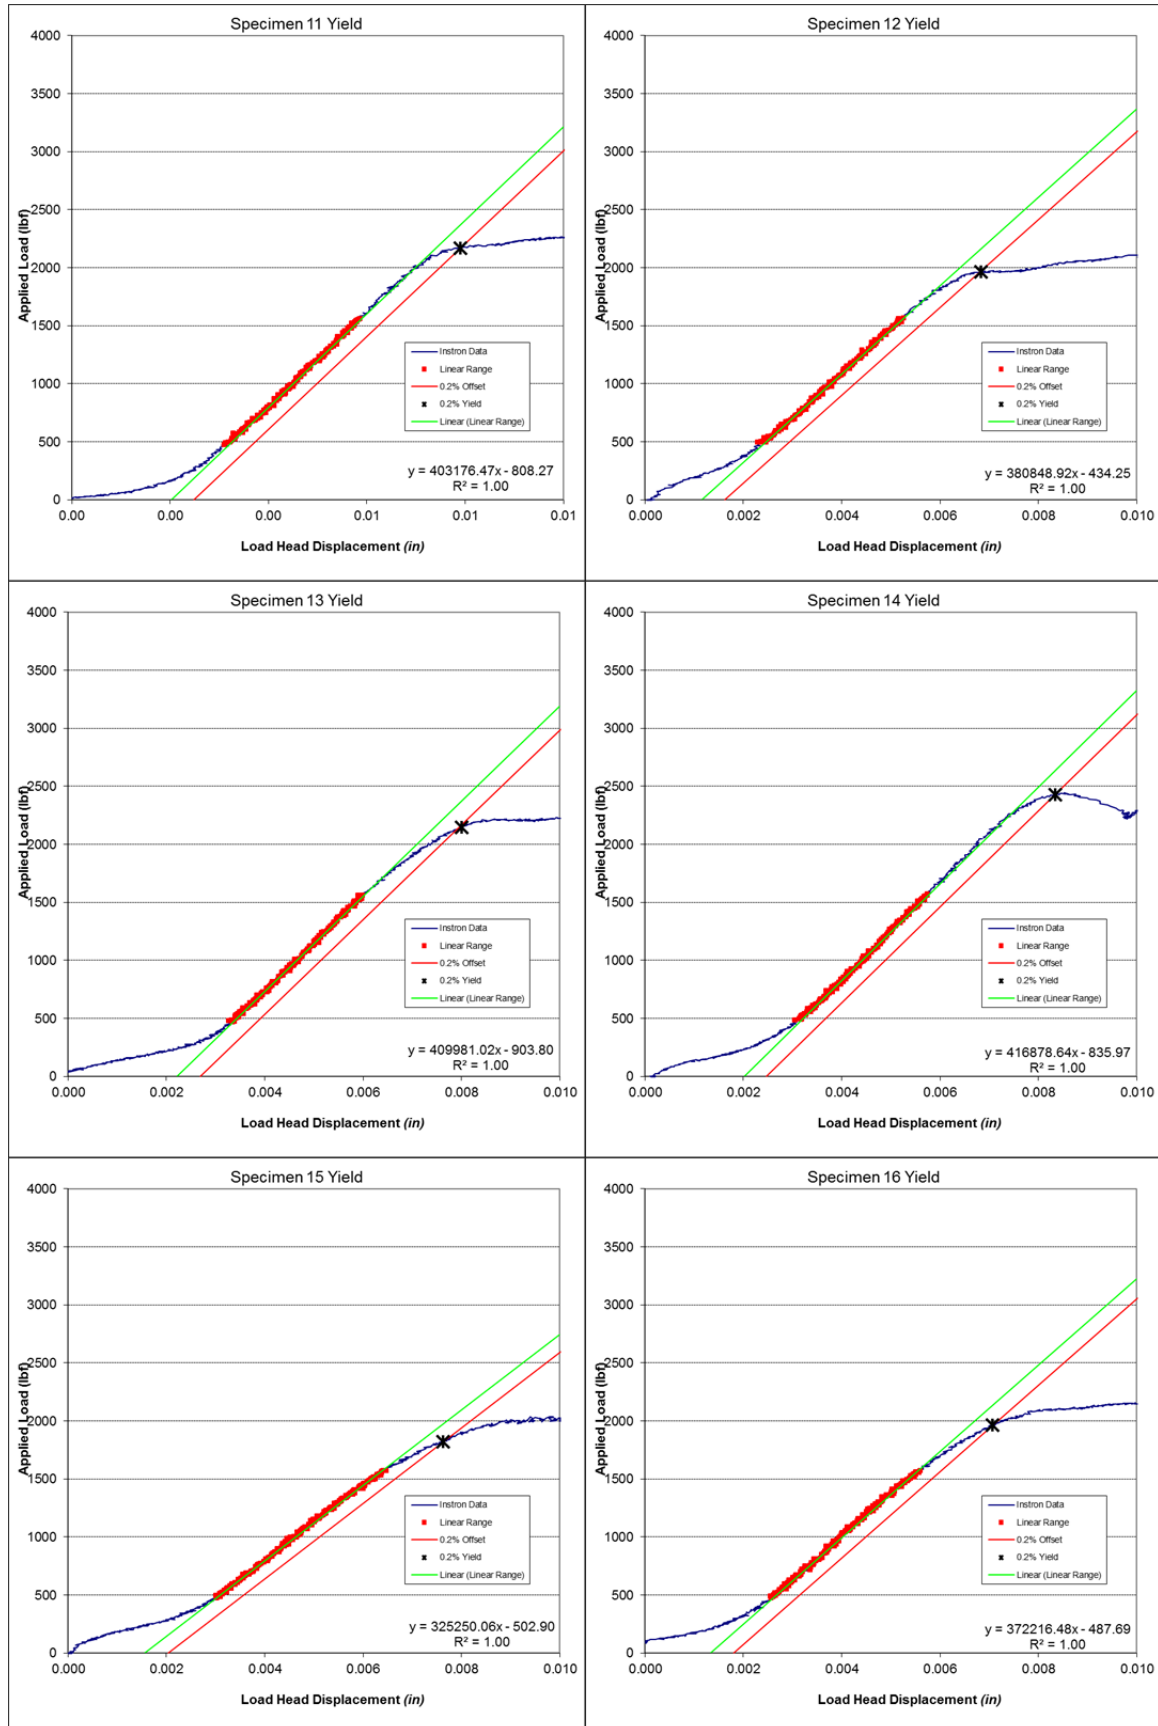


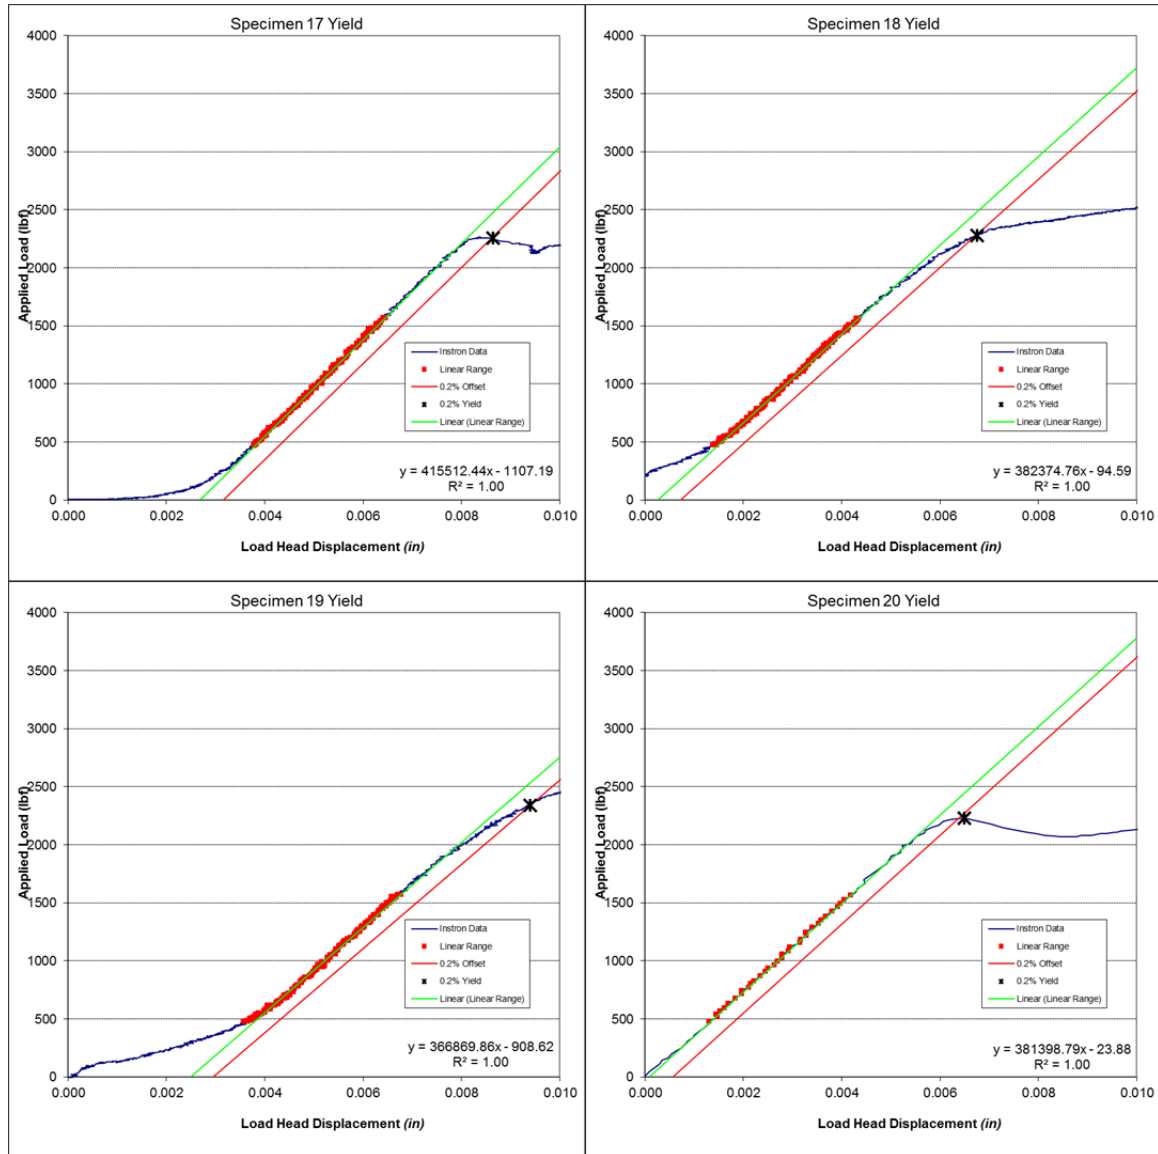


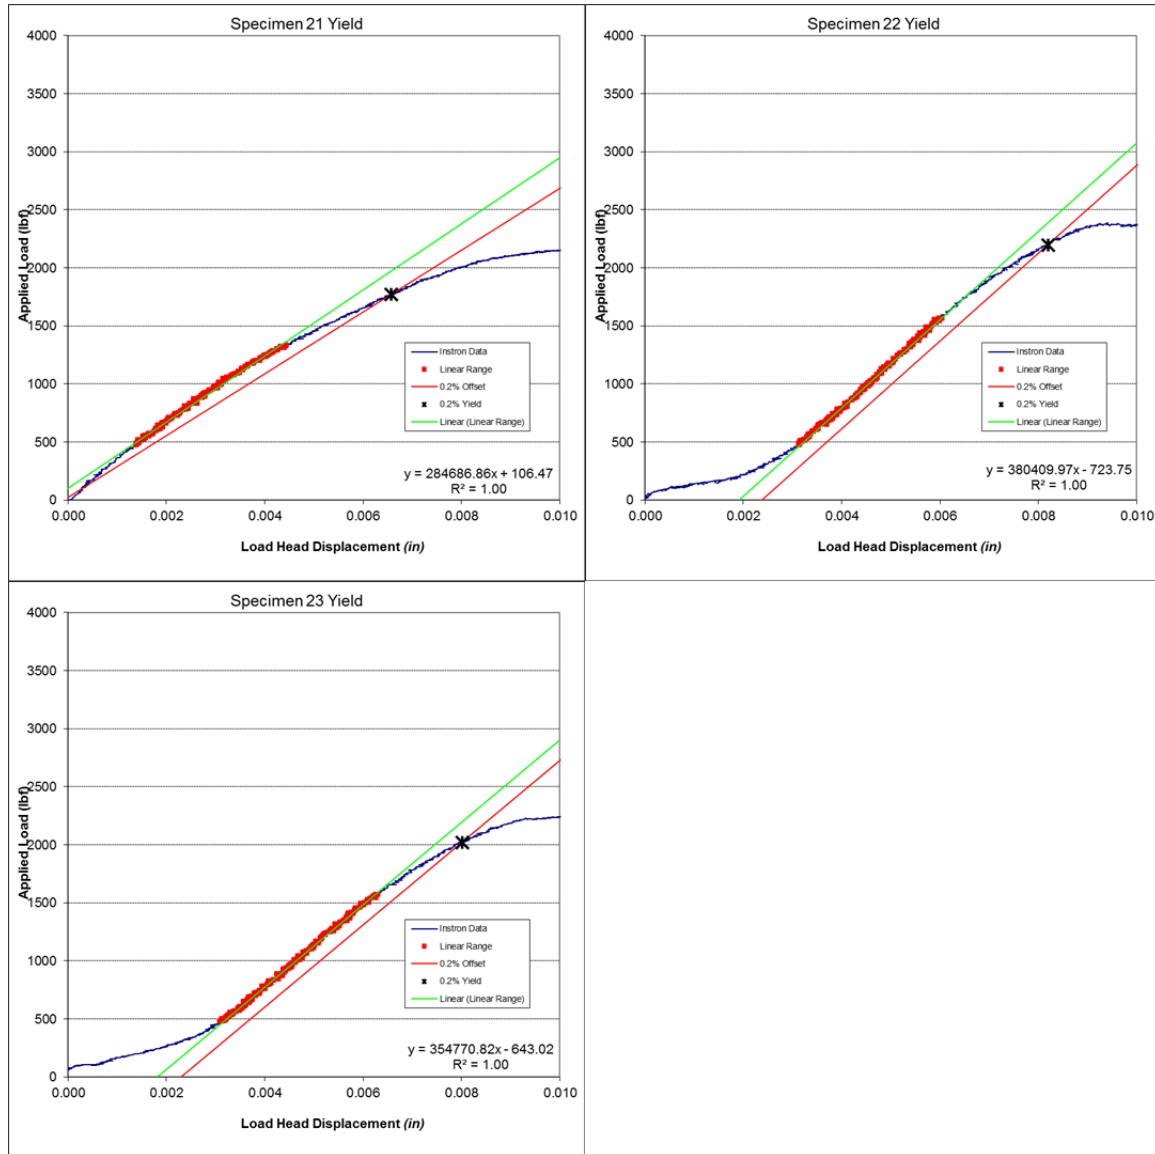



A.5 Engineering Stress vs. Approximate Engineering Strain Rate


The engineering stress is plotted against the approximate engineering strain rate for each rivet specimen in this appendix.

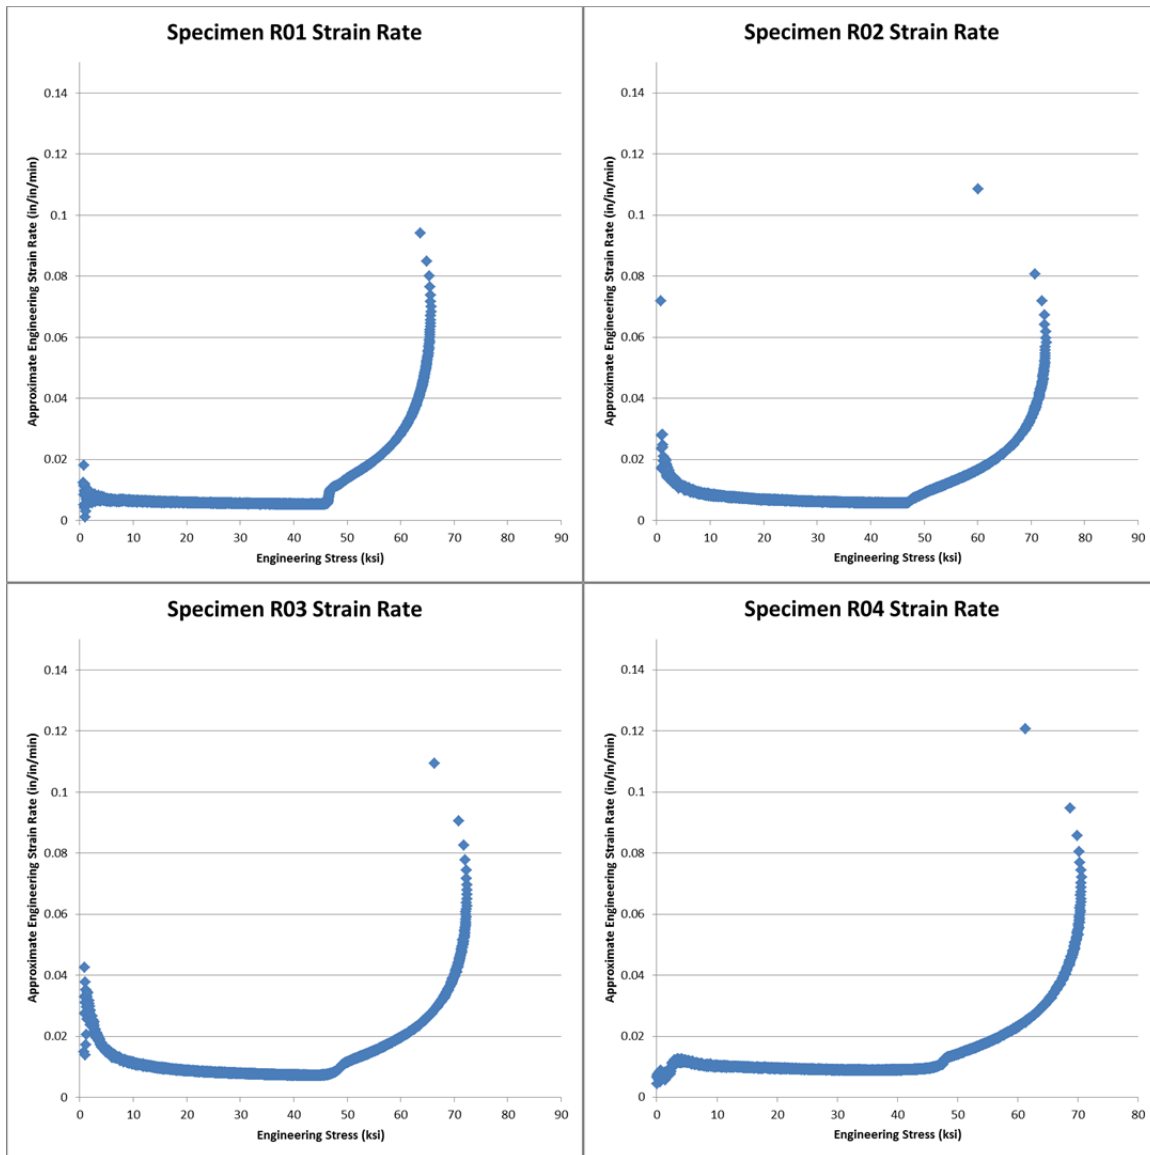

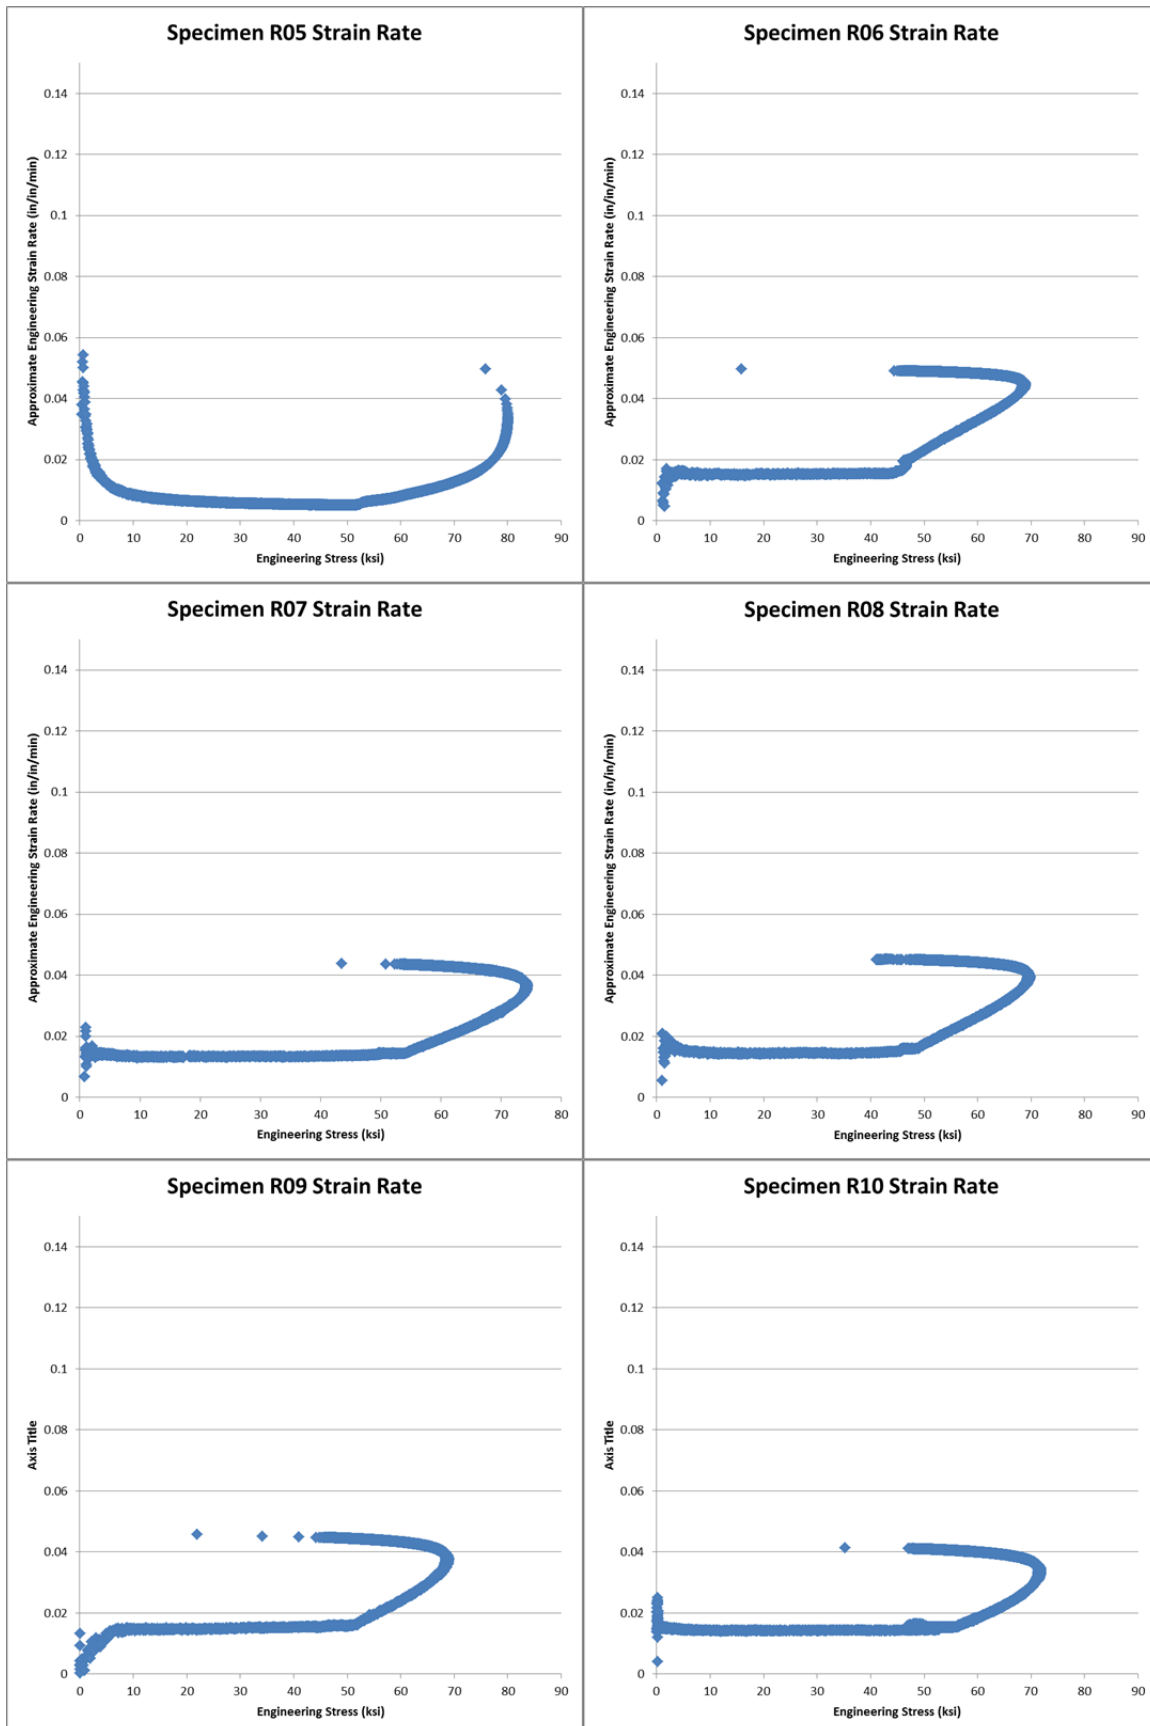

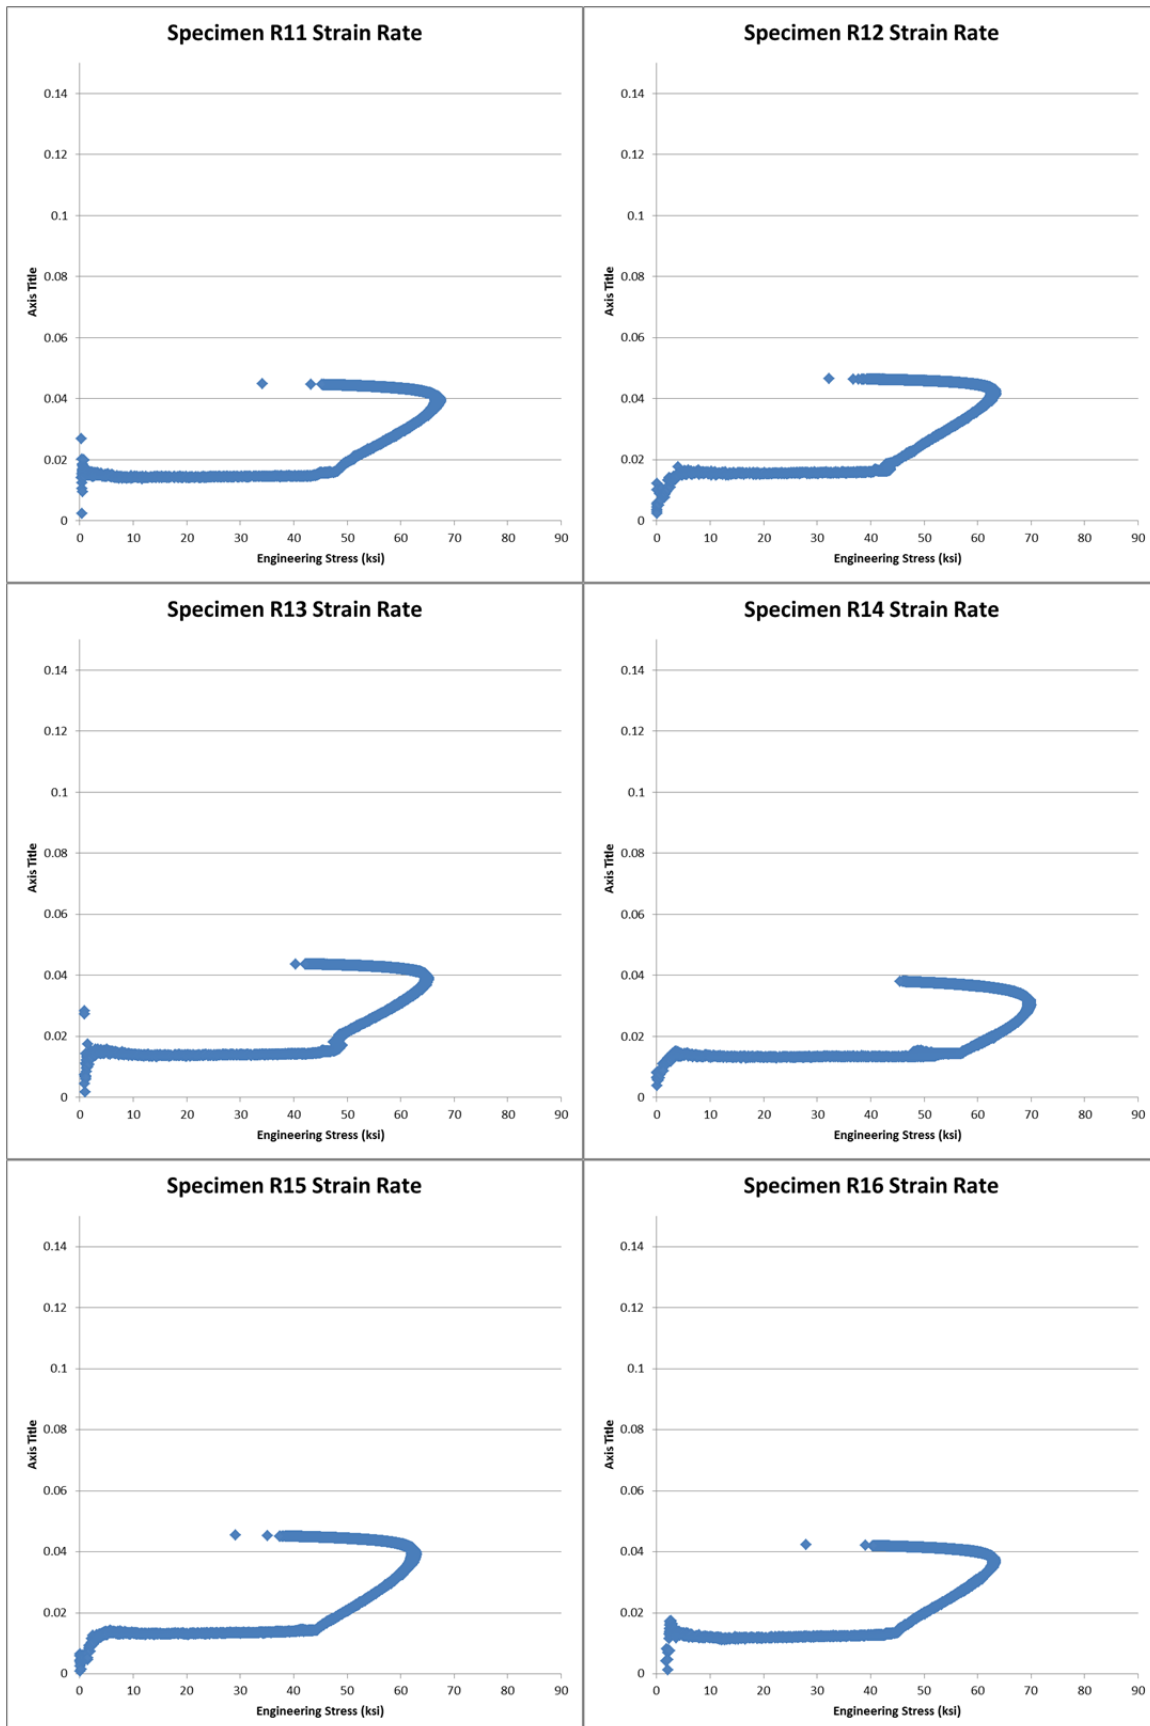

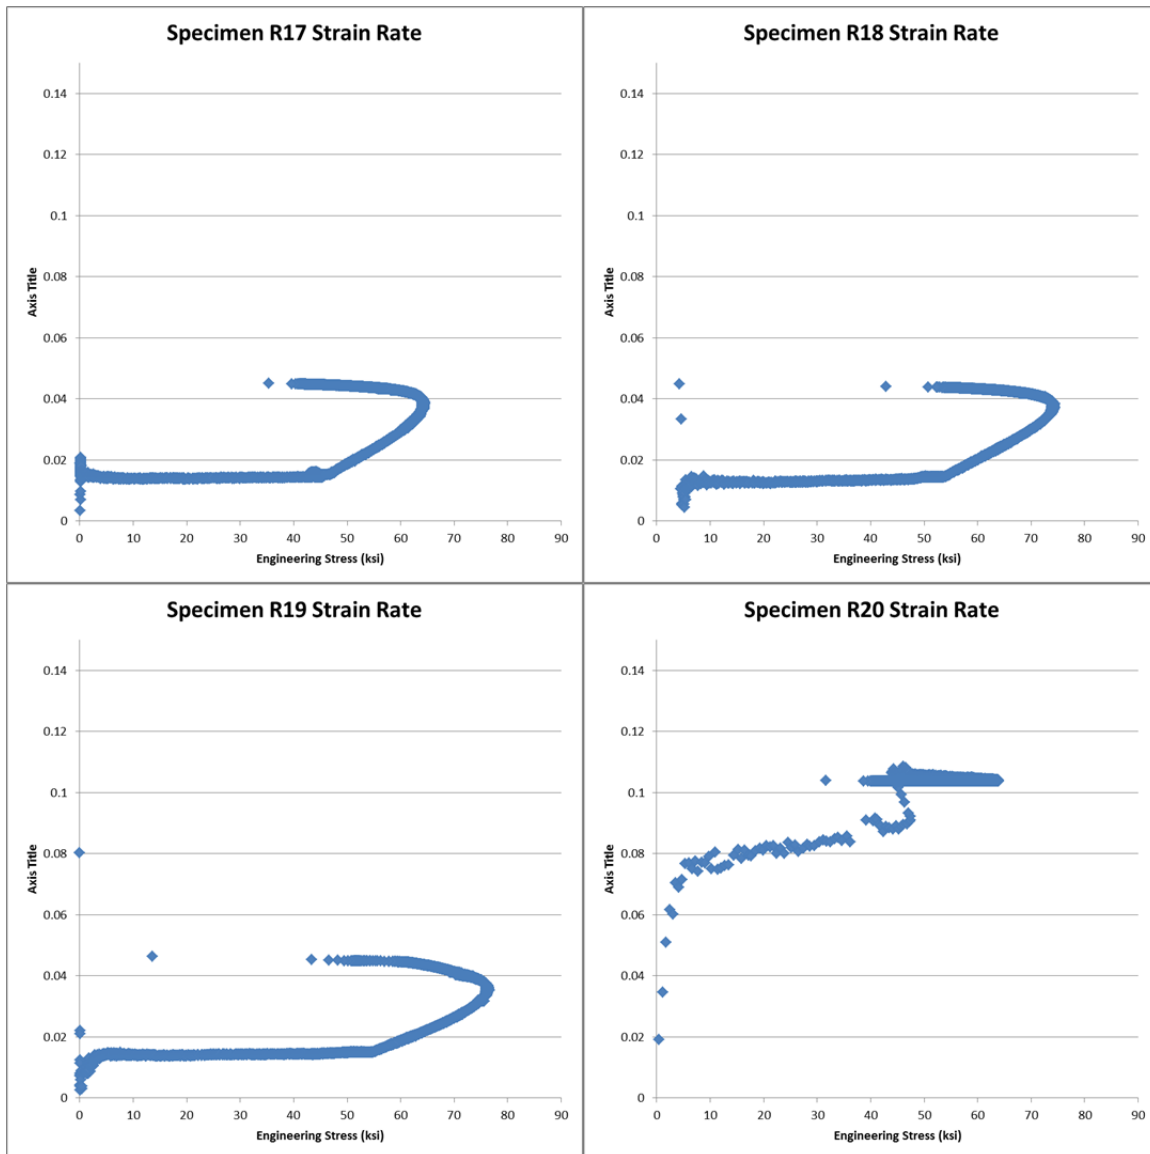

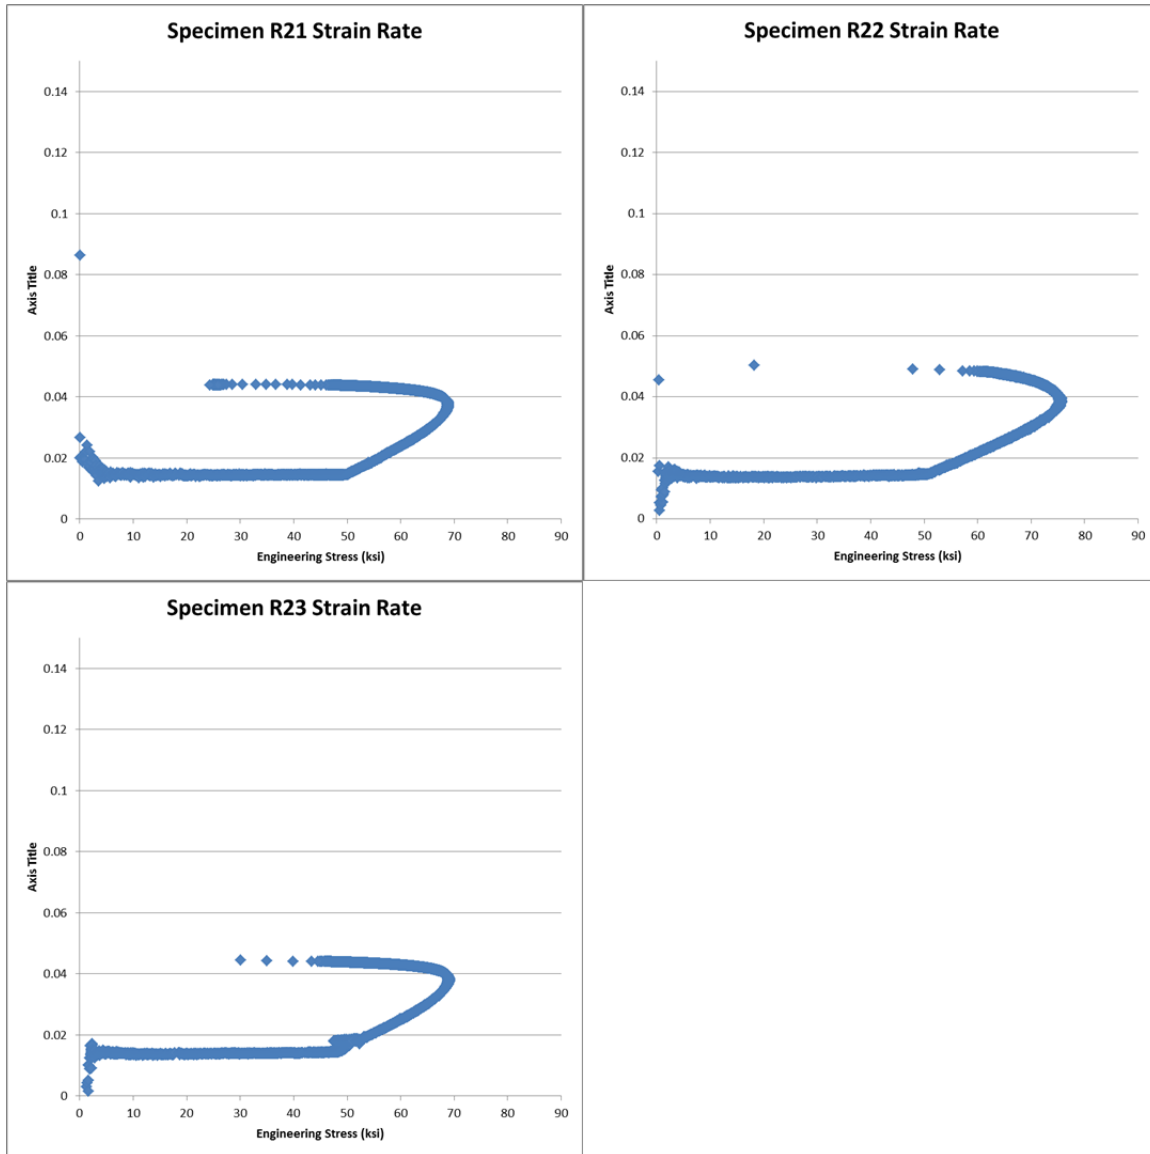

1. ASTM Standard F606/F606M, 2014, "Test Methods for Determining the Mechanical Properties of Externally and Internally Threaded Fasteners, Washers, Direct Tension Indicators, and Rivets," ASTM International West Conshohocken, PA, 2014, DOI: 10.1520/F0606_F0606M-14A., www.astm.org.
2. ASTM Standard E8/E8M, 2015, "Test Methods for Tension Testing of Metallic Materials," ASTM International West Conshohocken, PA, 2015, DOI: 10.1520/E0008_E0008M-15A., www.astm.org.
3. AASHTO. (2011) The Manual for Bridge Evaluation. Second Edition ed. Washington DC: AASHTO.